

Ecofriendly synthesis of silver nanoparticles by naringe leaf extract, study the antimicrobial activity against pathogenic bacteria

Esam J. Al-Kalifawi¹, Athraa H. Hasson¹, Susan A. R. Hasan¹, Tagreed M. Al-Saadi² and Entisar E. Al-Obodi³

¹Department of Biology, ²Department of physic, ³Department of Chemistry, College of Education for Pure Science Ibn-Alhethm, University of Baghdad, Iraq

Abstract

In the present study, environment friendly and cost effective silver nanoparticless were synthesized using the naringe (*Citrus aurantium*) leaf extract as the reducing and capping agent. The nanoparticless were characterized using UV-visble, FT-IR, XRD, and SEM methods. The surface plasmon resonance peaks in absorption spectra for silver colloidal solution showed that the absorption maximum range was at 390- 450 nm. The functional biomolecules such as carboxyl groups present in the seaweed responsible for the silver nanoparticles formation were characterized by FT-IR. The XRD results suggested that the crystallization of the bio-organic phase occurs on the surface of the silver nanoparticles or vice versa. The broadening of peaks in the XRD patterns was attributed to particle size effects and the average particles size about 25.17 nm. The results showed that silver nanoparticles synthesised by naringe (*Citrus aurantium*) leaf extract has effective antibacterial activities on the test isolates, the inhibition zone was 14 mm for *Enterobacter cloacae*, 10 mm for *Escherichia coli*, 25 mm for *Klebsiella pneumonia*, 18mm for *Proteus mirabilis*, *Bacillus sp.*, *Staphylococcus aureus* and *Streptococcus spp.* 9 mm for *Pseudomonas aeruginosa*. The antimicrobial activity of naringe leaf extract against test bacteria was negative. The study revealed that the silver nanoparticles synthesis by naringe (*Citrus aurantium*) leaf extract could be as a therapeutic agent for human microbial infections.

التخليق الصديق للبيئة لمنمنمات الفضة باستخدام مستخلص أوراق النارنج ودراسة فعاليتها المضادة للجراثيم

عصام جاسم الخليفاوي¹ و عدراء حميد حسون¹ و سوزان عبد الرحيم حسن¹ و تغريد مسلم الساعدي² و انتصار عليوي العبودي³
¹قسم علوم الحياة ، ²قسم الفيزياء، ³قسم الكيمياء / كلية التربية للعلوم الصرفة / جامعة بغداد / العراق.

الخلاصة

في الدراسة الحالية صنعت منمنمات الفضة بطريقة صديقة للبيئة واقل تكلفة، وذلك باستخدام مستخلص أوراق النارنج كعامل مختزل ومثبت. درست خصائص منمنمات الفضة باستخدام المطياف للأشعة فوق البنفسجية - المرئية والأشعة تحت الحمراء و حيود الأشعة السينية ومجهر القوة الذرية و المجهر الإلكتروني الماسح. أثبت الفحص بالمطياف أن ذروة الامتصاص عند مدى 390-450 نانومتر. اثبتت نتائج الفحص بالأشعة تحت الحمراء وجود مجموعات فعالة عديدة. نتائج الفحص بجهاز حيود الأشعة السينية تشير إلى طبيعة التشتت المتعدد من الجسيمات النانوية المحضرة بالطريقة البايولوجية. وتشير النتائج أن تبلور المرحلة البيولوجية العضوية يحدث على سطح الفضة النانوية أو العكس بالعكس. ويعزى توسيع قمم في أنماط حيود الأشعة السينية إلى تأثيرات حجم الجسيمات. تم مسح منمنمات الفضة المخلقة بمساعدة مستخلص أوراق النارنج بواسطة المجهر الإلكتروني الماسح ومنه نستنتج ان معدل

متوسط الحجم لمنمنمات الفضة كانت 25.17 نانوميتر وشوهدت ذات شكل كروي. أظهرت النتائج ان منمنمات الفضة المخلقة بوساطة مستخلص أوراق النارج تمثلك نشاط مضاد للجراثيم، حيث كان قطر التثبيط 14 ملم للأمعانية المخرقية، 10 ملم للأشريكية القولونية، 25 ملم لكليبيلا الرئوية، 18 ملم للمتقلبة الرائحة، العصوية س، المكورات العنقودية الذهبية والعقدية س. 9 ملم للزائفة الزنجارية. وكانت فعالية مستخلص أوراق النارج تجاه الجراثيم سلبية. وكشفت الدراسة أن تخليق منمنمات الفضة بوساطة مستخلص أوراق النارج يمكن أن تكون كعامل علاجي للعدوى الميكروبية الإنسان

Introduction

Nanotechnology is a rapidly growing science of producing and utilizing nano-sized particles. A number of approaches are available for the synthesis of silver nanoparticles, such as thermal decomposition [1], electrochemical [2] microwave assisted process [3] and green chemistry [4]. Many of the nanoparticle synthesis or production methods of nanoparticles involve the use of hazardous chemicals, low material conversions and high energy requirements. So, a growing need to develop an environmentally friendly process for nanoparticle synthesis without using toxic chemicals is gaining importance. Biosynthetic methods employing either microorganisms or plant extracts have emerged as a simple and viable alternative to chemical synthetic procedures and physical methods. Several microorganisms, such as bacteria, fungi and yeasts, have come up as nano factories, synthesizing metal nanoparticles of Ag and Au. However, the use of plants for the fabrication of nanoparticles has drawn attention, because of its rapid, economical, eco-friendly protocol, and it provides a single step technique for the biosynthesis process [5]. Biological approaches using microorganisms and plants or plant extracts for metal nanoparticle synthesis have been suggested as valuable alternatives to chemical methods. An important branch of biosynthesis of nanoparticles is the application of plant extract to the biosynthesis reaction. Synthesis of quasi spherical silver nanoparticles used a purified apiin compound, extracted from henna leaf at ambient conditions [6]. Using green tea, *C. sinensis* extracts, as a reducing and stabilizing agent, gold nanoparticles and silver nanostructures were produced in aqueous solution at ambient conditions [7]. Plant extracts from live alfalfa, the broths of lemongrass, geranium leaves and others have served as green reactants in Ag NP synthesis. The reaction of aqueous AgNO₃ with an aqueous extract of leaves of a common ornamental geranium plant, *Pelargonium graveolens*, gave Ag NPs after 24 h [8]. Silver nanoparticles ranging from 55 to 80 nm in size, and triangular or spherical gold nanoparticles, were fabricated using the novel sundried biomass of *Cinnamomum canphora* leaf [5]. A simple procedure applying Aloe vera leaf extract has been used for the synthesis of gold nanotriangle and spherical silver nanoparticles. Aloe vera extract showed more spherical silver nanoparticles with increasing the amount of added extract [9]. Silver nanoparticles were successfully synthesized using the latex of *Jatropha curcas*. The plant, *Jatropha curcas*, is commercially important, as bio-diesel is extracted from its seeds on an industrial scale. Crude latex was obtained by cutting the green stems of *J. curcas* plants [10]. In another research work, biosynthesis of silver nanoparticles was also conducted using *Cycas* leaf extract [11]. *Cycas* is rich in flavonoids, broadly belonging to the class of phenolic compounds.

Citrus aurantium is the botanical name for a plant commonly referred to as Bitter orange, Sour orange, Neroli, Chongcao, and Seville orange. Citrus plant is native to

tropical Asia but it is also found in all tropical and subtropical country. It is easily available plant showing a wide range of uses in treatment of various diseases. The major active biological constituents in Citrus herbs are flavonoids, especially hesperidin, naringin and alkaloids, mainly synephrine, with beneficial medical effects on human health [12]. It has been used for their essential oil in foods and perfumes. *C. aurantium* is also used in herbal medicine as a stimulant and appetite suppressant. It has also been used in traditional Chinese medicine to treat nausea, indigestion, and constipation, cancer, cardiovascular effect, sedative. However, what has made bitter orange well known and popularized is the claim that it replaces the banned ephedra stimulant, without the ephedra side effects. Because of this, *C. aurantium* is a popular weight loss ingredient used in a wide variety of diet pills and fat [13].

With the emergence and increase of microbial organisms resistant to multiple antibiotics, and the continuing emphasis on health-care costs, many researchers have tried to develop new, effective antimicrobial reagents free of resistance and cost. Such problems and needs have led to the resurgence in the use of Ag-based antiseptics that may be linked to broad-spectrum activity and far lower propensity to induce microbial resistance than antibiotics [14]. The antibacterial effects of Ag salts have been noticed since antiquity [15] and Ag is currently used to control bacterial growth in a variety of applications, including dental work, catheters, and burn wounds [16, 17].

The present work has focused on the development of the easy synthesis of silver nanoparticles by an environmentally friendly procedure. In Iraq the Bitter orange (*Citrus aurantium*) called Naringe; Naringe leaf extract was used for the silver nanoparticles synthesis, and evaluation of their antibacterial activity against various human multi drug resistant pathogenic bacteria.

Materials and Methods

Collection of pathogens

We are collected multiple antibiotic-resistant isolates, which included *Escherichia coli*, *Proteus mirabilis*, *Klebsiella pneumonia*, *Streptococcus sp.*, *Enterobacter cloacae*, *Bacillus sp.*, *Pseudomonas aeruginosa*, and *Staphylococcus aureus* used for the antimicrobial activity from microbiology diagnosis laboratory, Al-Numan hospital.

Synthesis of silver nanoparticles

For the synthesis of silver nanoparticles, we used Naringe (*Citrus aurantium*) leaf extract for reducing and capping agent which is taken from College of Education for Pure Science Ibn -Al- Haitham, Plants garden and silver nitrate (AgNO_3) purchased from Merck limited, India. Naringe leaf extract was prepared by taking 25g of thoroughly washed and finely crushed Naringe leaf mixed with 100ml deionized water in 500 ml of Erlenmeyer flask and then boiling the mixture for 10 min before finally decanting it. For the reduction of Ag^+ ions, 5ml of Naringe leaf extract was mixed to 45 ml of 0.002M aqueous of AgNO_3 solution drop wise with constant stirring at 50-60°C and until the colour change [18].

Characterization of silver nanoparticles

1- UV-Vis Spectra analysis:

The reduction of pure Ag^+ ions was monitored by measuring the UV-Vis spectrum of the reaction medium after 30 min. UV-Vis spectrophotometer is procured from Shimadzu. A small aliquot of the sample was taken for UV-Vis spectrum analysis (350-

750 nm). The maximum absorbance spectrum of As-Ag nanoparticles was observed at 455 nm [18].

2- Fourier Transform Infra Red Spectroscopy (FT-IR)

FT-IR measurements were carried out using Perkin (8300 FT-IR Shimadzu Spectrophotometer) the range from 4000 cm^{-1} to 400 cm^{-1} . After complete reduction of AgNO_3 ions by Naringe leaf extract, the mixture was centrifuged at 10000 rpm for 10 min to remove protein or other bioorganic compounds that were present in the solution. The silver nanoparticles pellet obtained was air dried. The dried nanoparticles were mixed with the potassium bromide (KBr) to make thin pellets and were used for FT-IR analysis in transmittance mode [18].

3- X-Ray Diffraction (XRD) analysis

Resulting solution of the developed nanoparticles of silver was centrifuged at 10,000 rpm for 30 min. The solid residues of Ag NPs were washed twice with double distilled water and then dried at 80°C to obtain powder Ag NPs used for X-ray powder diffraction measurements. The powder X-ray diffraction (XRD) patterns were recorded on (Shimadzu XRD-6000) with copper radiation (Cu K_α , $1.5406\text{ \AA}$) at 40 kV and 30 mA [18].

4- SEM Analysis of Silver Nanoparticles

Scanning Electron Microscopic (SEM) analysis was done using (Inspect S 50) SEM machine. Thin films of the sample were prepared on a carbon coated copper grid by just dropping a very small amount of the sample on the grid [18].

Determination of antimicrobial activity

Antibacterial activity of the silver nanoparticles by using Naringe (*Citrus aurantium*) leaf extract was evaluated by the well agar diffusion method [19]. The bacterial cultures were adjusted to 0.5 McFarland turbidity standards and inoculated onto Mueller Hinton agar (MHA, Oxoid) plates. A sterile cork borer was used to make 2 well (8 mm in diameter) on the MHA plates. Aliquots of 100 μl of silver nanoparticles solution were applied in one of the wells in the culture plates previously seeded with the test organisms. The cultures were incubated at 37°C for 24 h. A well was made in each of the culture plates and filled with 100 μl of Naringe leaf extract as a control. Antimicrobial activity was determined by measuring the zone of inhibition around each well (excluding the diameter of the well). For each extract, three replicate trials were conducted against each organism.

Results and Discussion

The reduction of Ag^+ into Ag-NPs during exposure to water extract of Naringe (*Citrus aurantium*) leaf extract was able to be followed by the color change. The fresh suspension of Naringe leaf extract was yellow. However, after the addition of AgNO_3 and stirring for one hour at room temperature, the emulsion turned dark brown. The color changes in aqueous solutions are due to the surface-plasmon resonance (SPR) phenomenon (Figure 1B and C). The result obtained in this investigation is interesting because it can serve as a foundation in terms of identification of potential forest plants for synthesizing Ag-NPs.



Figure (1). Photograph of Silver nitrate solution (A), Naringe (*Citrus aurantium*) leaf extract (B) and silver/ Naringe (*Citrus aurantium*) leaf extract (C) emulsions after one hour of stirring time.

UV-Vis Spectrophotometry

The Formation of metal nanoparticles by reduction of the aqueous metal ions during exposure of Naringe (*Citrus aurantium*) leaf extract may be easily followed by UV-Vis spectroscopy (UV- shimadzu spectrophotometer). UV-Vis absorption spectrum of silver nanoparticles in the presence of Naringe (*Citrus aurantium*) leaf extract is shown in figure (2). The surface plasmon resonance peaks in absorption spectra for silver colloidal solution showed that the absorption maximum range was at 390- 450 nm, suggesting that the nanoparticles were dispersed in the aqueous solution with no evidence for aggregation in UV-Vis absorption spectrum Figure (2).

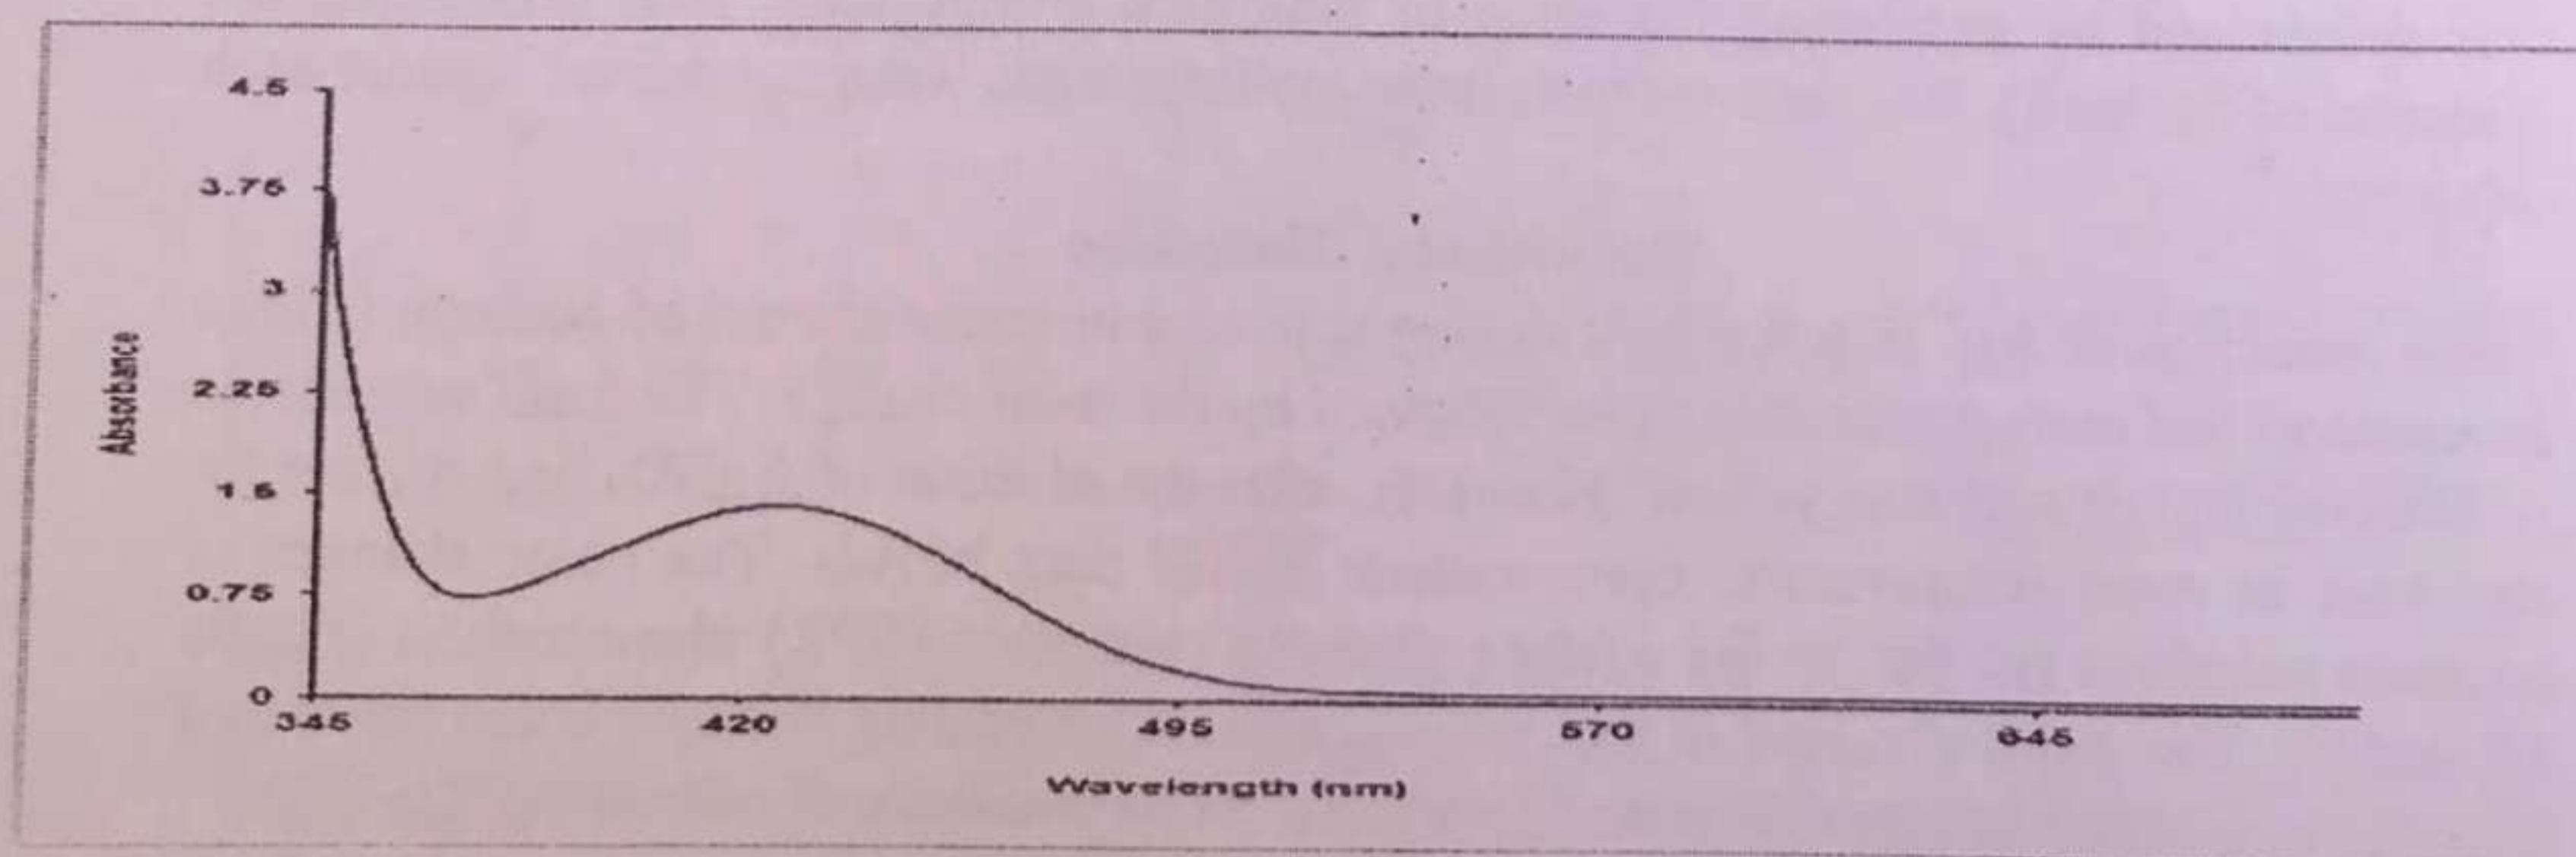


Figure (2). UV-Vis absorption spectra of Silver nanoparticles synthesized by exposure of Naringe (*Citrus aurantium*) leaf extract with 0.002M silver nitrate.

Fourier Transform Infra Red Spectroscopy

The results of FTIR analysis of this study show different stretches of bonds shown at different peaks; 3327.21—N—H stretch, 1641.42 —C=C, and 1211.30—C=O. Figure 3 shows the peaks near 3440 cm^{-1} , and 2968 cm^{-1} assigned to OH stretching and aldehydic C—H stretching, respectively. The weaker band at 1629 cm^{-1} corresponds to amide I arising due to carbonyl stretch in proteins. The peak at 1051 cm^{-1} corresponds to C—N stretching vibration of the amine. The peak near 1743 cm^{-1} corresponds to C=C stretching (non conjugated). The peak near 866 cm^{-1} assigned to C=CH₂ and the peaks near 678 cm^{-1} and 638 cm^{-1} assigned to CH out of plane bending vibrations are substituted ethylene systems —CH=CH. FTIR spectra of silver nanoparticles exhibited prominent peaks at 1641, and 1382 cm^{-1} . The spectra showed sharp and strong absorption band at 1641 cm^{-1} assigned to the stretching vibration of (NH) C=O group [20].

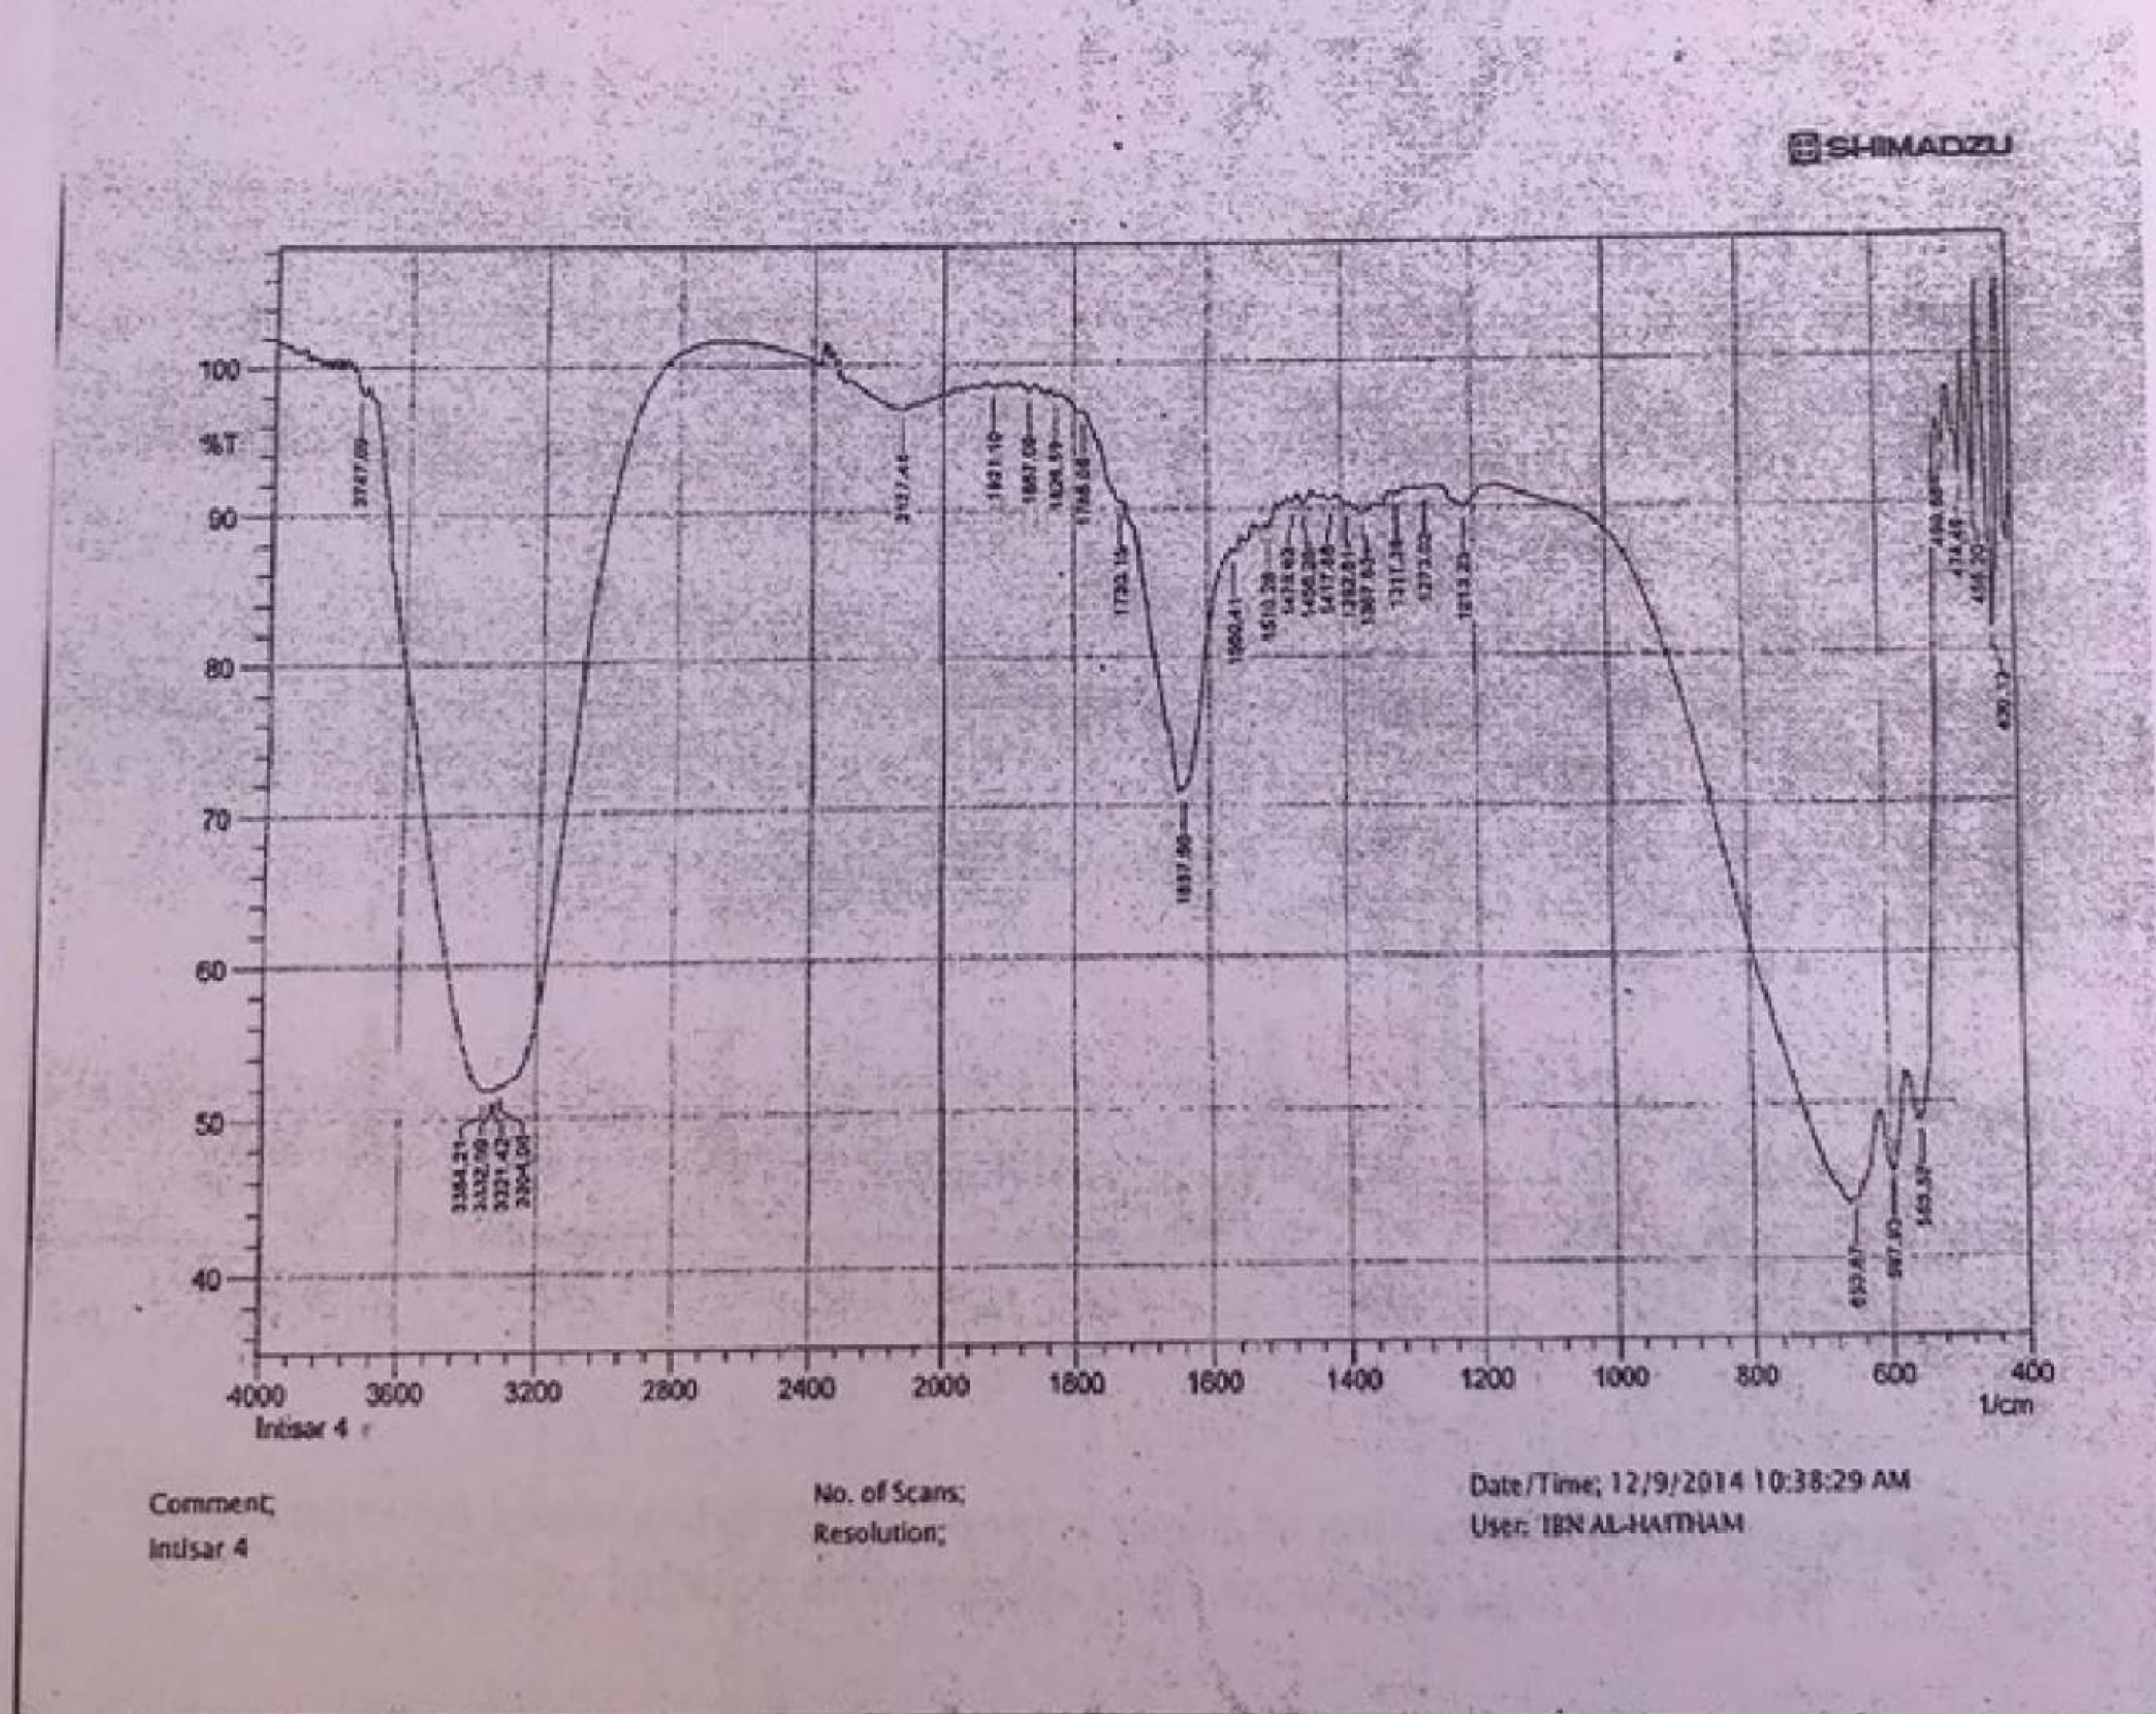


Figure (3). Fourier Transform Infra Red Spectroscopy image of Silver nanoparticles synthesized by exposure of Naringe (*Citrus aurantium*) leaf extract with 0.002M silver nitrate.

Powder X-ray diffraction

Figure (4) shows the XRD patterns of Ag-NPs. The X-ray diffraction patterns of the Ag-NPs synthesized by using AgNO_3 and using the Naringe (*Citrus aurantium*) leaf extract as the reducing and capping agent are shown in Fig. 4. All the reflections correspond to pure silver metal with face centered cubic symmetry. The reflections were indexed as (111), (200) and (220) with the corresponding 2θ values of 38.128, 44.315 and 64.468 respectively (JCPDS 04-0783). The intensity of peaks reflected the high degree of crystallinity of the silver nanoparticles. However, the diffraction peaks were broad indicating that the crystallite size is very small. The average particle size of Ag-NPs can be calculated using the Debye - Scherrer equation [21].

$$D = K \lambda / \beta \cos \theta$$

where K is the Scherrer constant with value from 0.9 to 1 (shape factor), λ is the X-ray wavelength ($1.5418 \text{ \AA}$), β is the width of the XRD peak at half-height and θ is the Bragg angle and D is the grain size. From the Scherrer equation, the average crystallite size of Ag-NPs is (25.17 nm).

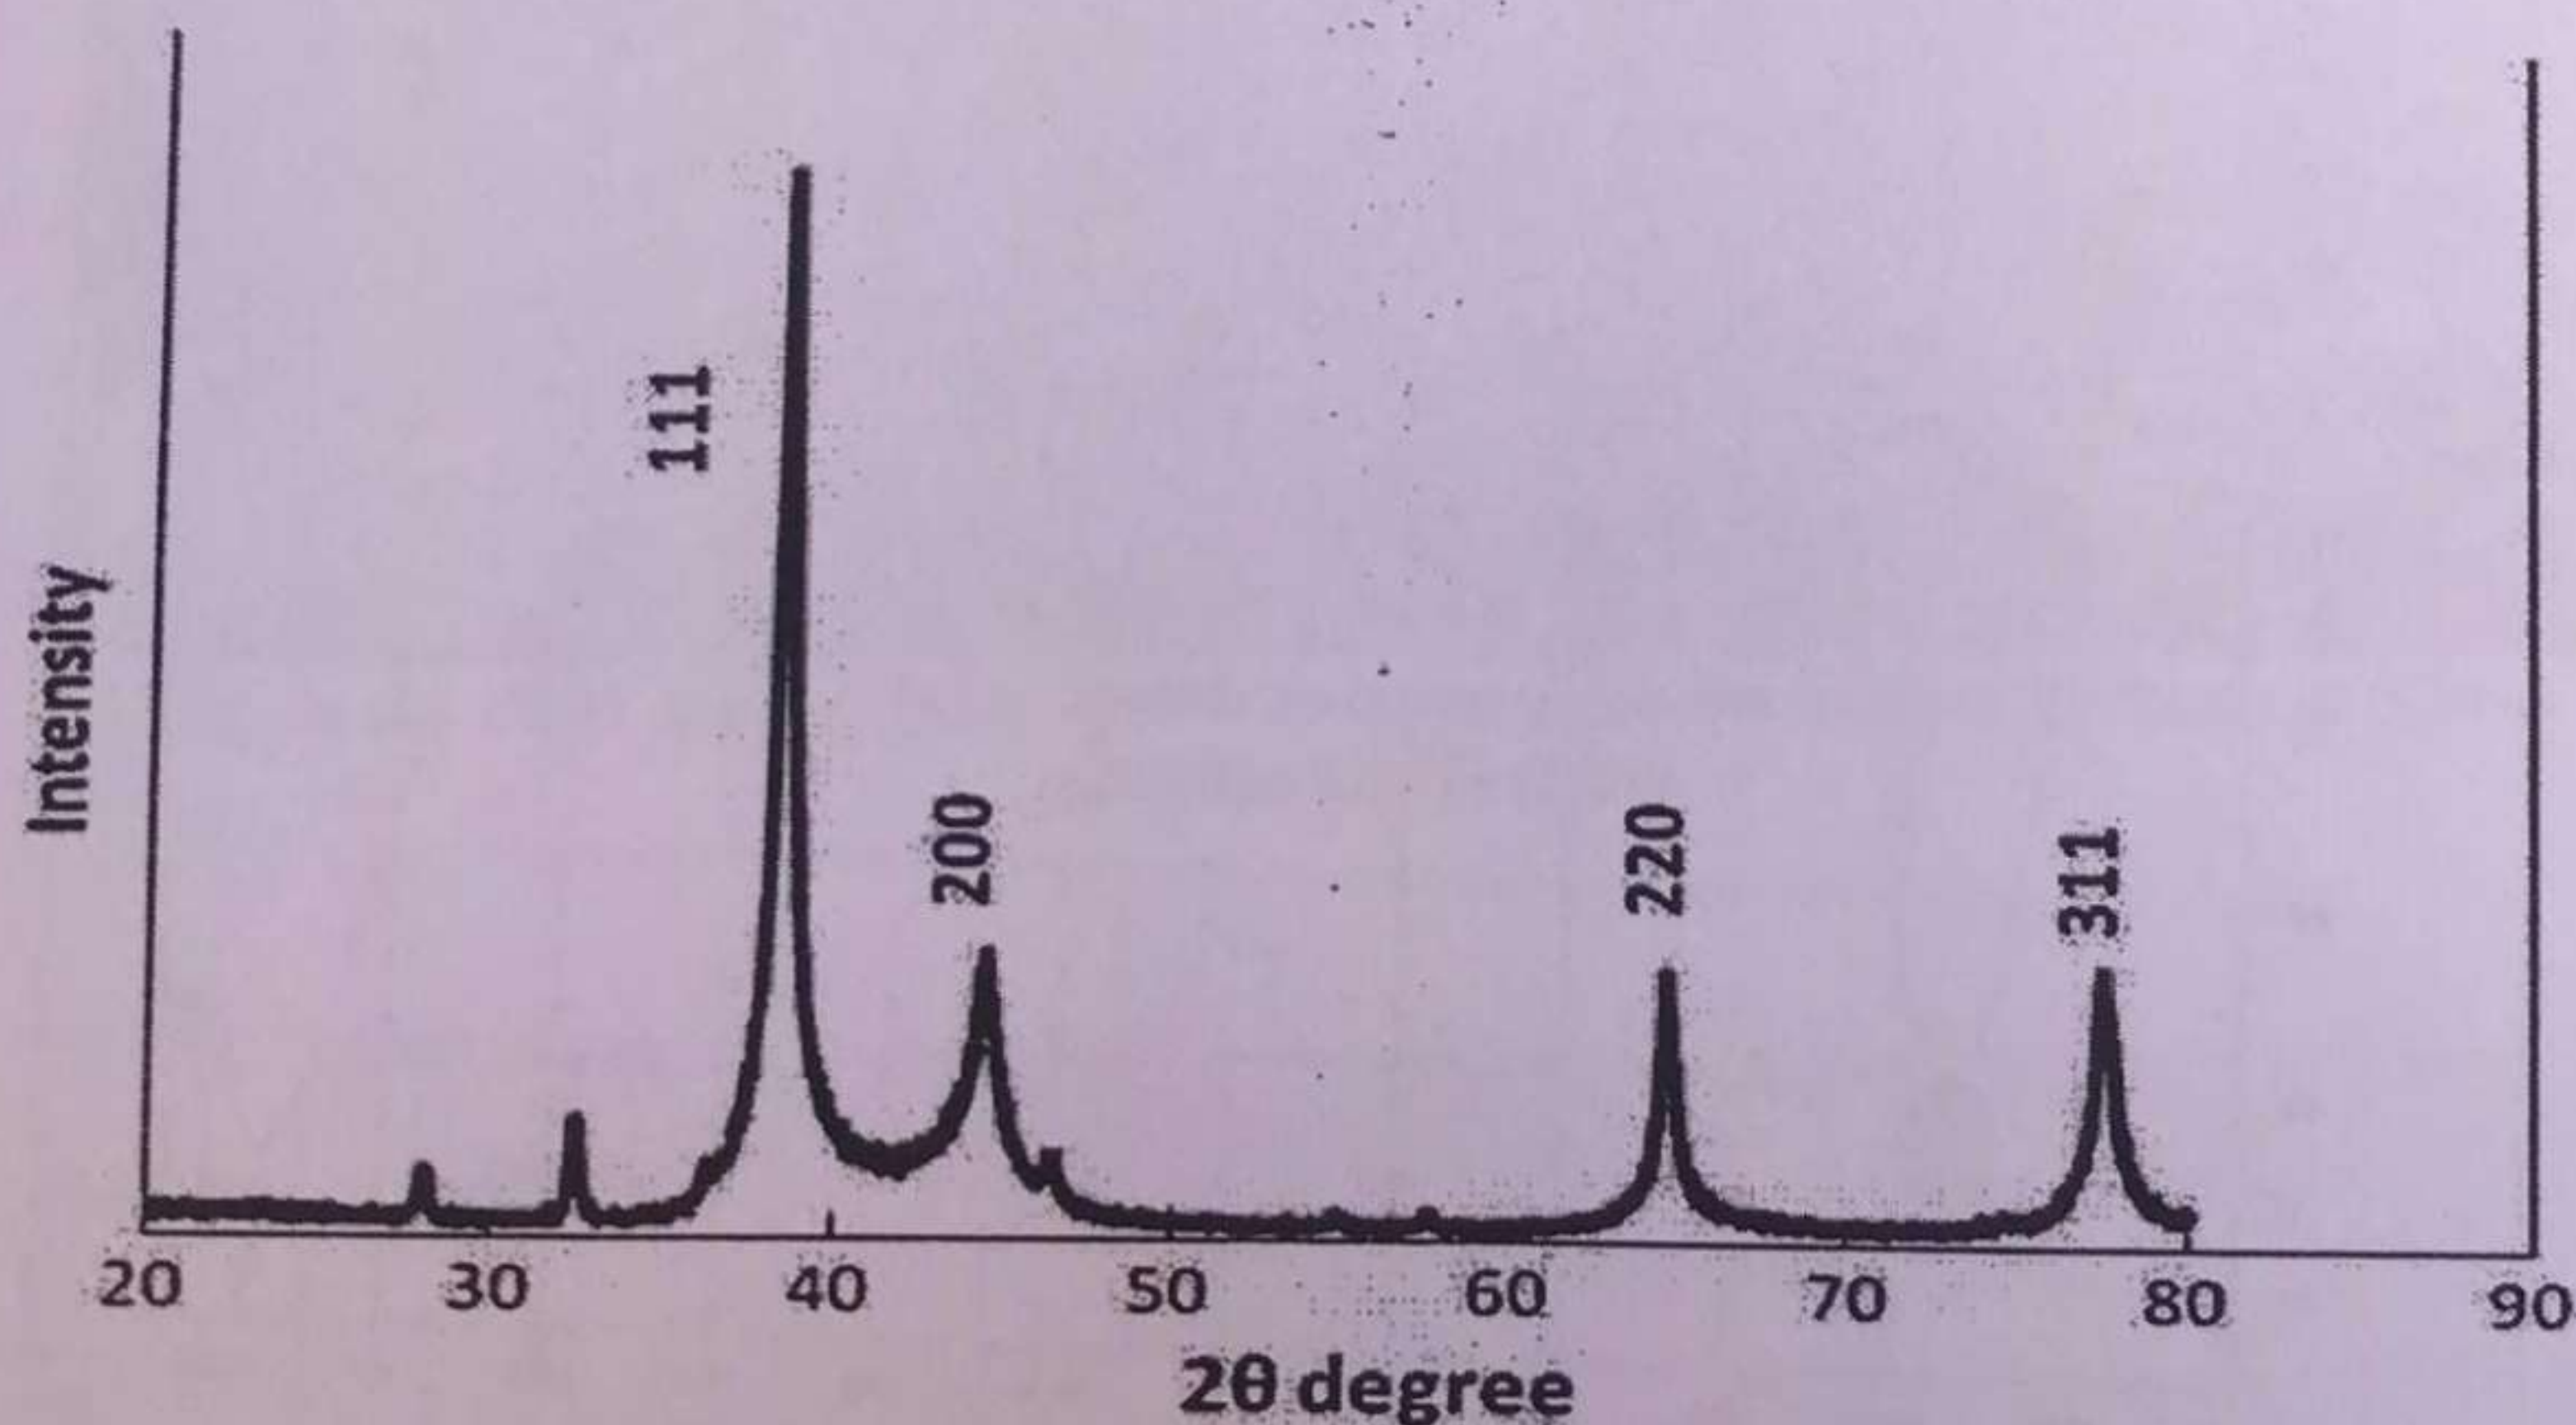


Figure (4). X ray diffraction of Silver nanoparticles synthesized by exposure of Naringe (*Citrus aurantium*) leaf extract with 0.002M silver nitrate.

SEM analysis of Silver nanoparticles

The silver nanoparticles synthesized by the help of Naringe (*Citrus aurantium*) leaf extract were scanned by SEM as shown in figure (5). It reveals that silver nanoparticles seem to be spherical in morphology and particles form cluster. It is easy to notice that the examined particles consist of a number of smaller objects of a few micrometers in size. However, we did not manage to examine the structure of the

observed nanoparticles because of difficulties connected with getting higher magnification. In Figure (6), a standard EDX spectrum recorded on the examined sample is shown. In the middle part of the presented spectrum a strong peak located at 3 KV. This maxima is directly related to the silver characteristic line L. The maximum located on the left part of the spectrum at 0.2 kV clearly comes from carbon. Quantitative analysis proved high silver contents (100%) in the examined samples the result shown in table (1).

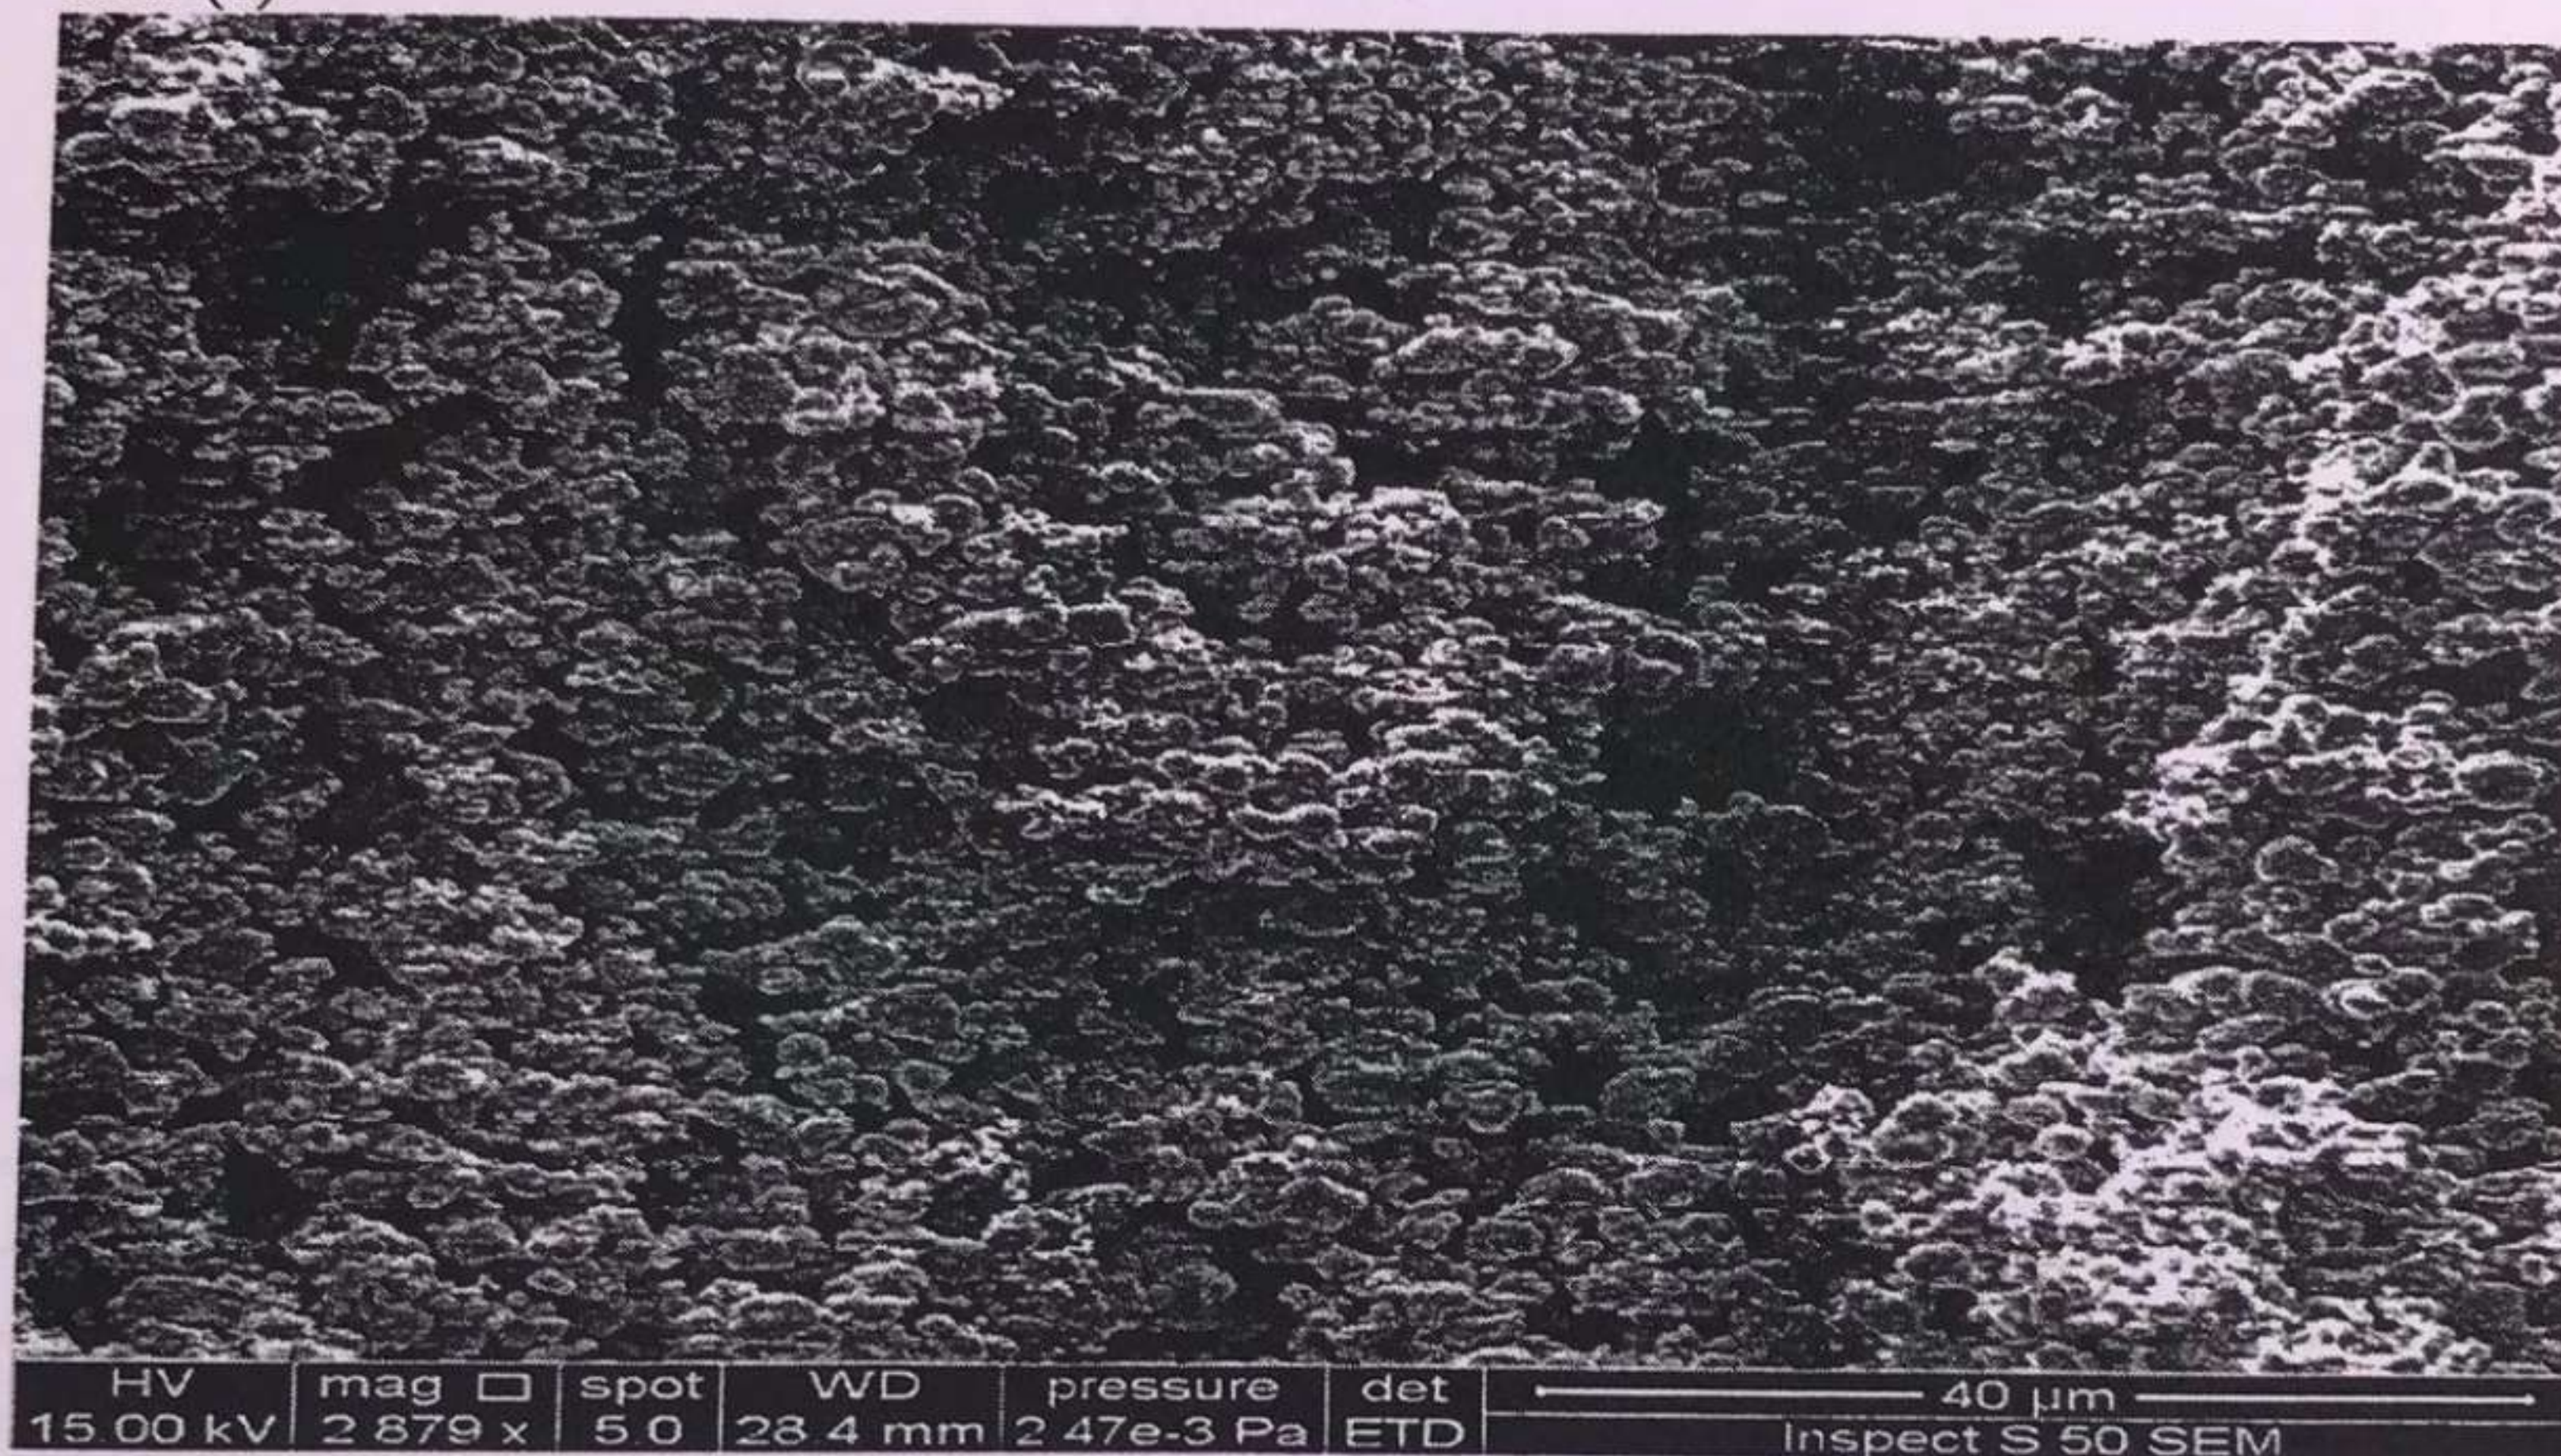


Figure (5). SEM micrographs of silver nanoparticles synthesised by Naringe (*Citrus aurantium*) leaf extract.

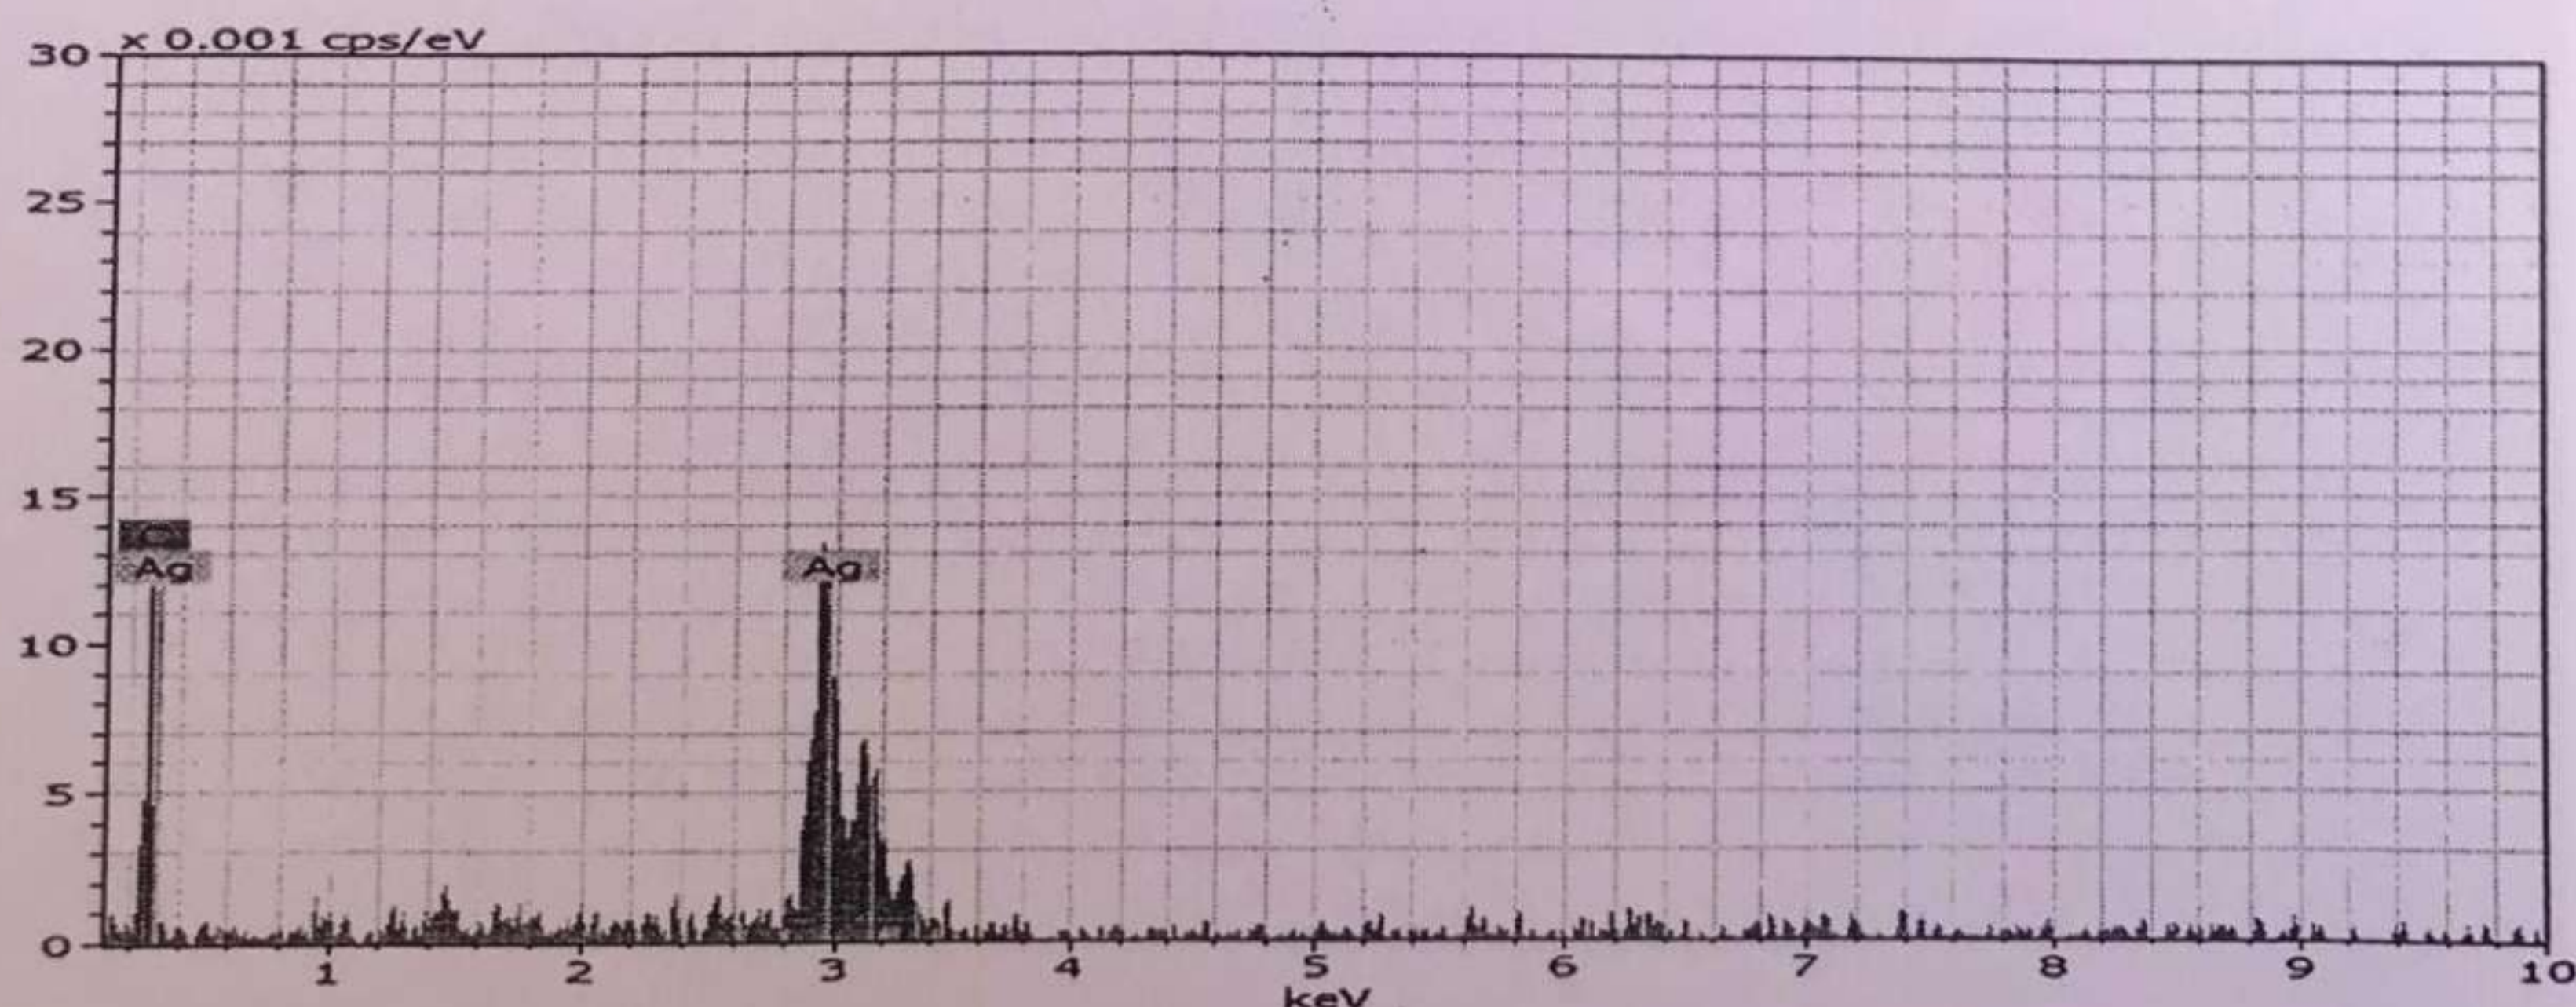


Figure (6).EDX characteristic spectrum obtained for silver powder.

Table (1) shows the elements in silver nanoparticles

Element	AN	series	[wt.%]	[norm. wt.%]	[norm. at.%]
Carbon	6	K-series	0	0	0
Silver	47	L-series	75.13866	100	100
		Sum:	75.13866	100	100

The data in Table (2) and Figure (8-11) shows that silver nanoparticles synthesised by Naringe (*Citrus aurantium*) leaf extract has effective antibacterial activities on the test isolates as indicated by the diameter of their zone of inhibition. The inhibition zone was 14 mm for *Enterobacter cloacae*, 10 mm for *Escherichia coli*, 25 mm for *Klebsiella pneumonia*, 18mm for *Proteus mirabilis*, *Bacillus sp.*, *Staphylococcus aureus* and *Streptococcus spp.* 9 mm for *Pseudomonas aeruginosa*. The antimicrobial activity of Naringe (*Citrus aurantium*) leaf extract against test bacteria was negative.

Table (2). The inhibitory activity of the Ag-NPs synthesis by Naringe (*Citrus aurantium*) leaf extract against the tested bacteria as demonstrated by diameters of the inhibition zone (mm)*.

Isolated bacteria	Zone of Inhibition	
	Naringe leaf extract	Naringe leaf extract / Ag-NPs
<i>Enterobacter cloacae</i>	0	14
<i>Escherichia coli</i>	0	10
<i>Klebsiella pneumonia</i>	0	25
<i>Proteus mirabilis</i>	0	18
<i>Pseudomonas aeruginosa</i>	0	9
<i>Bacillus sp.</i>	0	18
<i>Staphylococcus aureus</i>	0	18
<i>Streptococcus spp.</i>	0	18

* Zone of inhibition, including the diameter of the cup plate method (8.0 mm). The recorded value is mean value of 3 replicates.

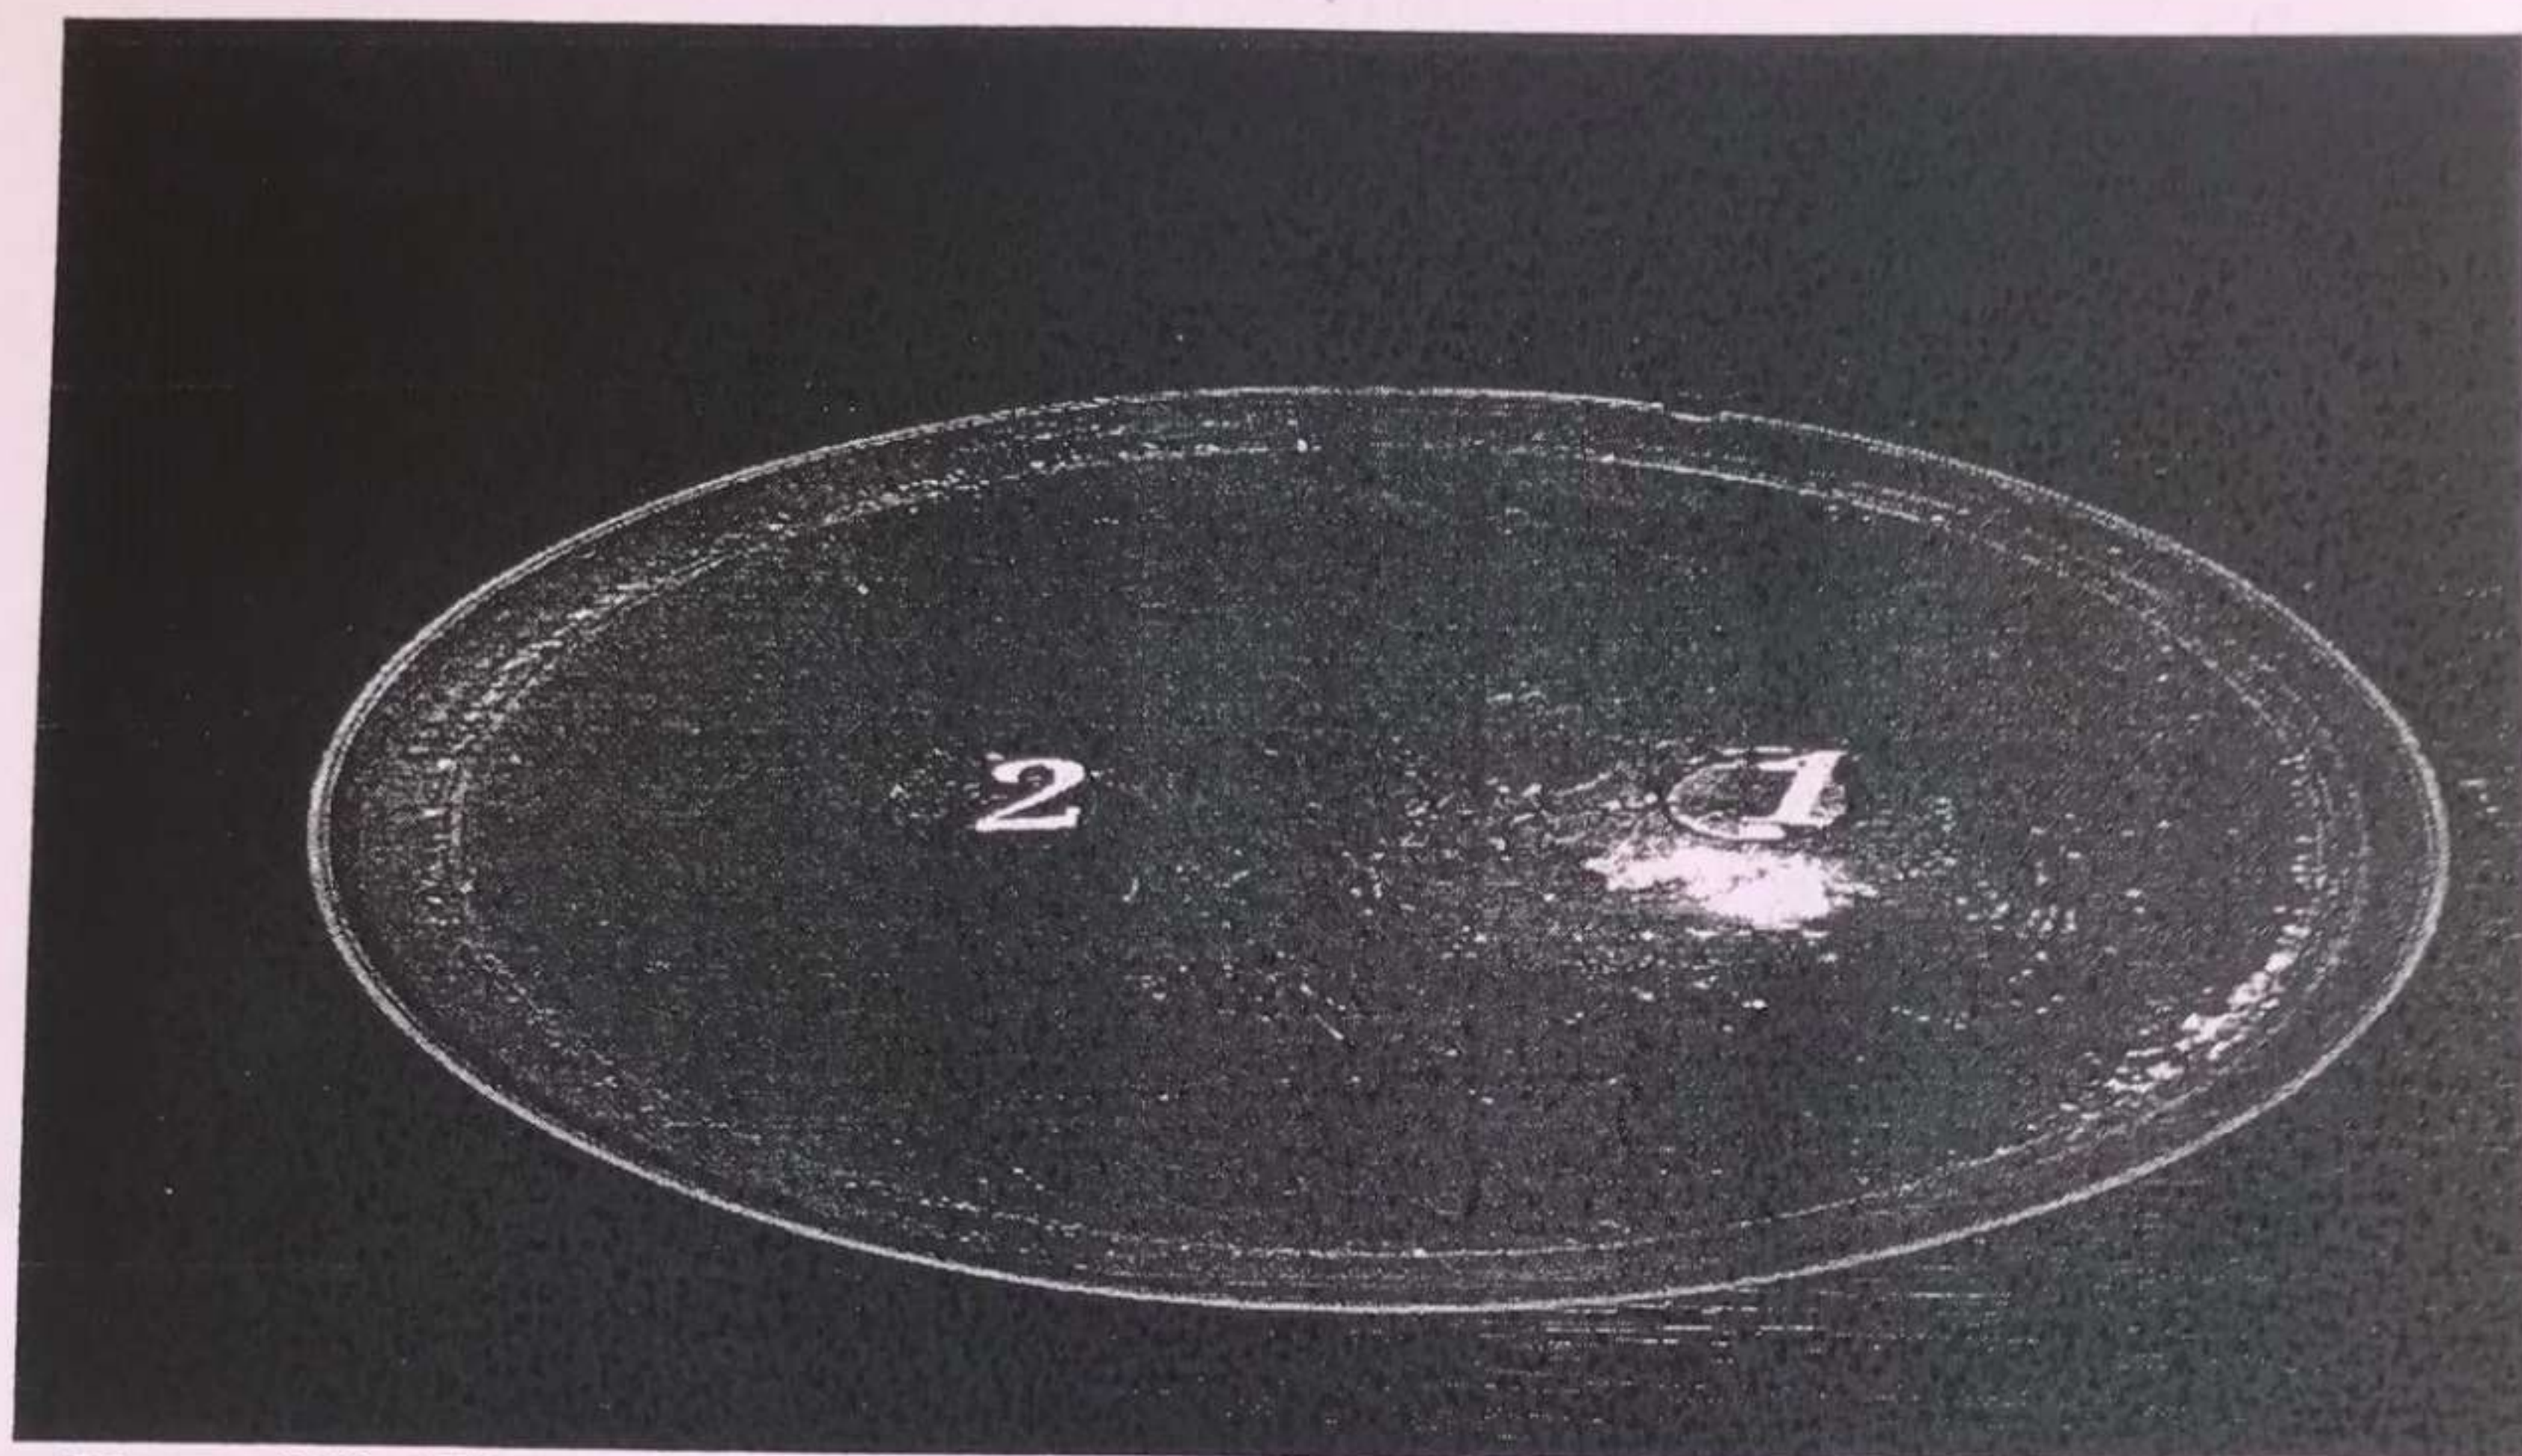


Figure (10). The antibacterial effect of Silver nanoparticles synthesis by Naringe leaf extract (1), Naringe leaf extract (2) using the test bacterium *Escherichia coli*.

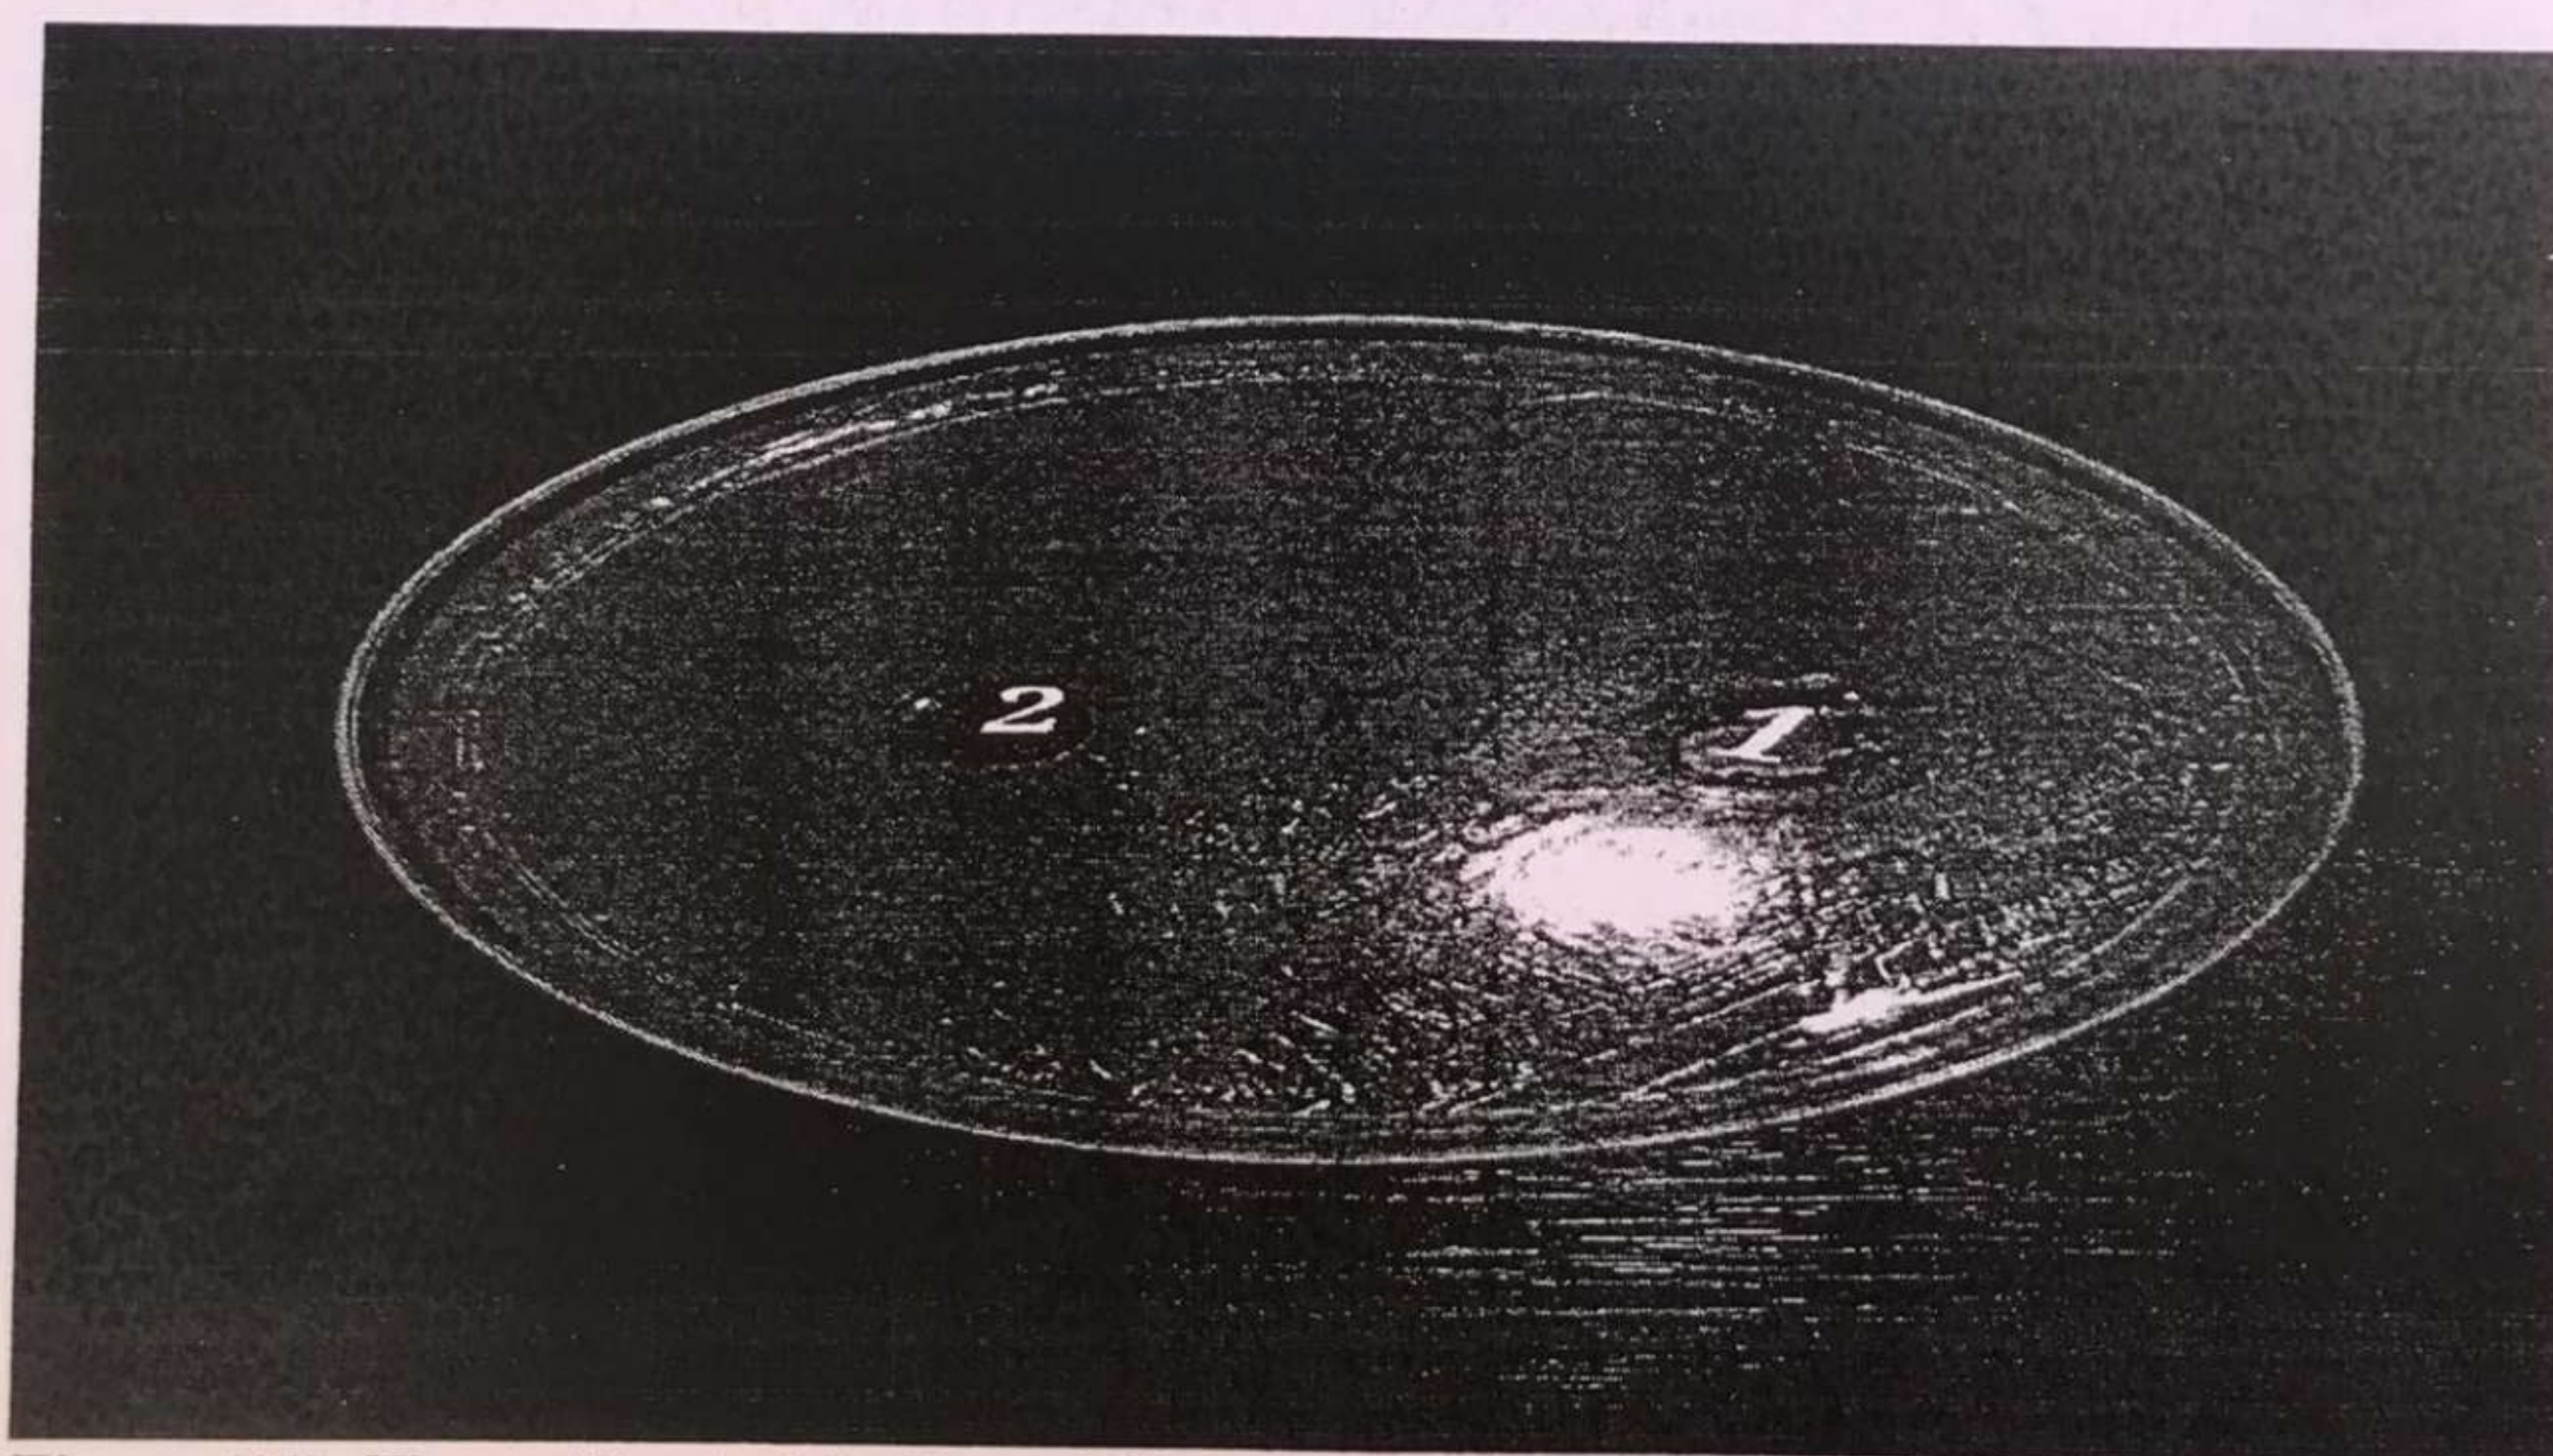


Figure (11). The antibacterial effect of Silver nanoparticles synthesis by Naringe leaf extract (1), Naringe leaf extract (2) using the test bacterium *Pseudomonas aeruginosa*.

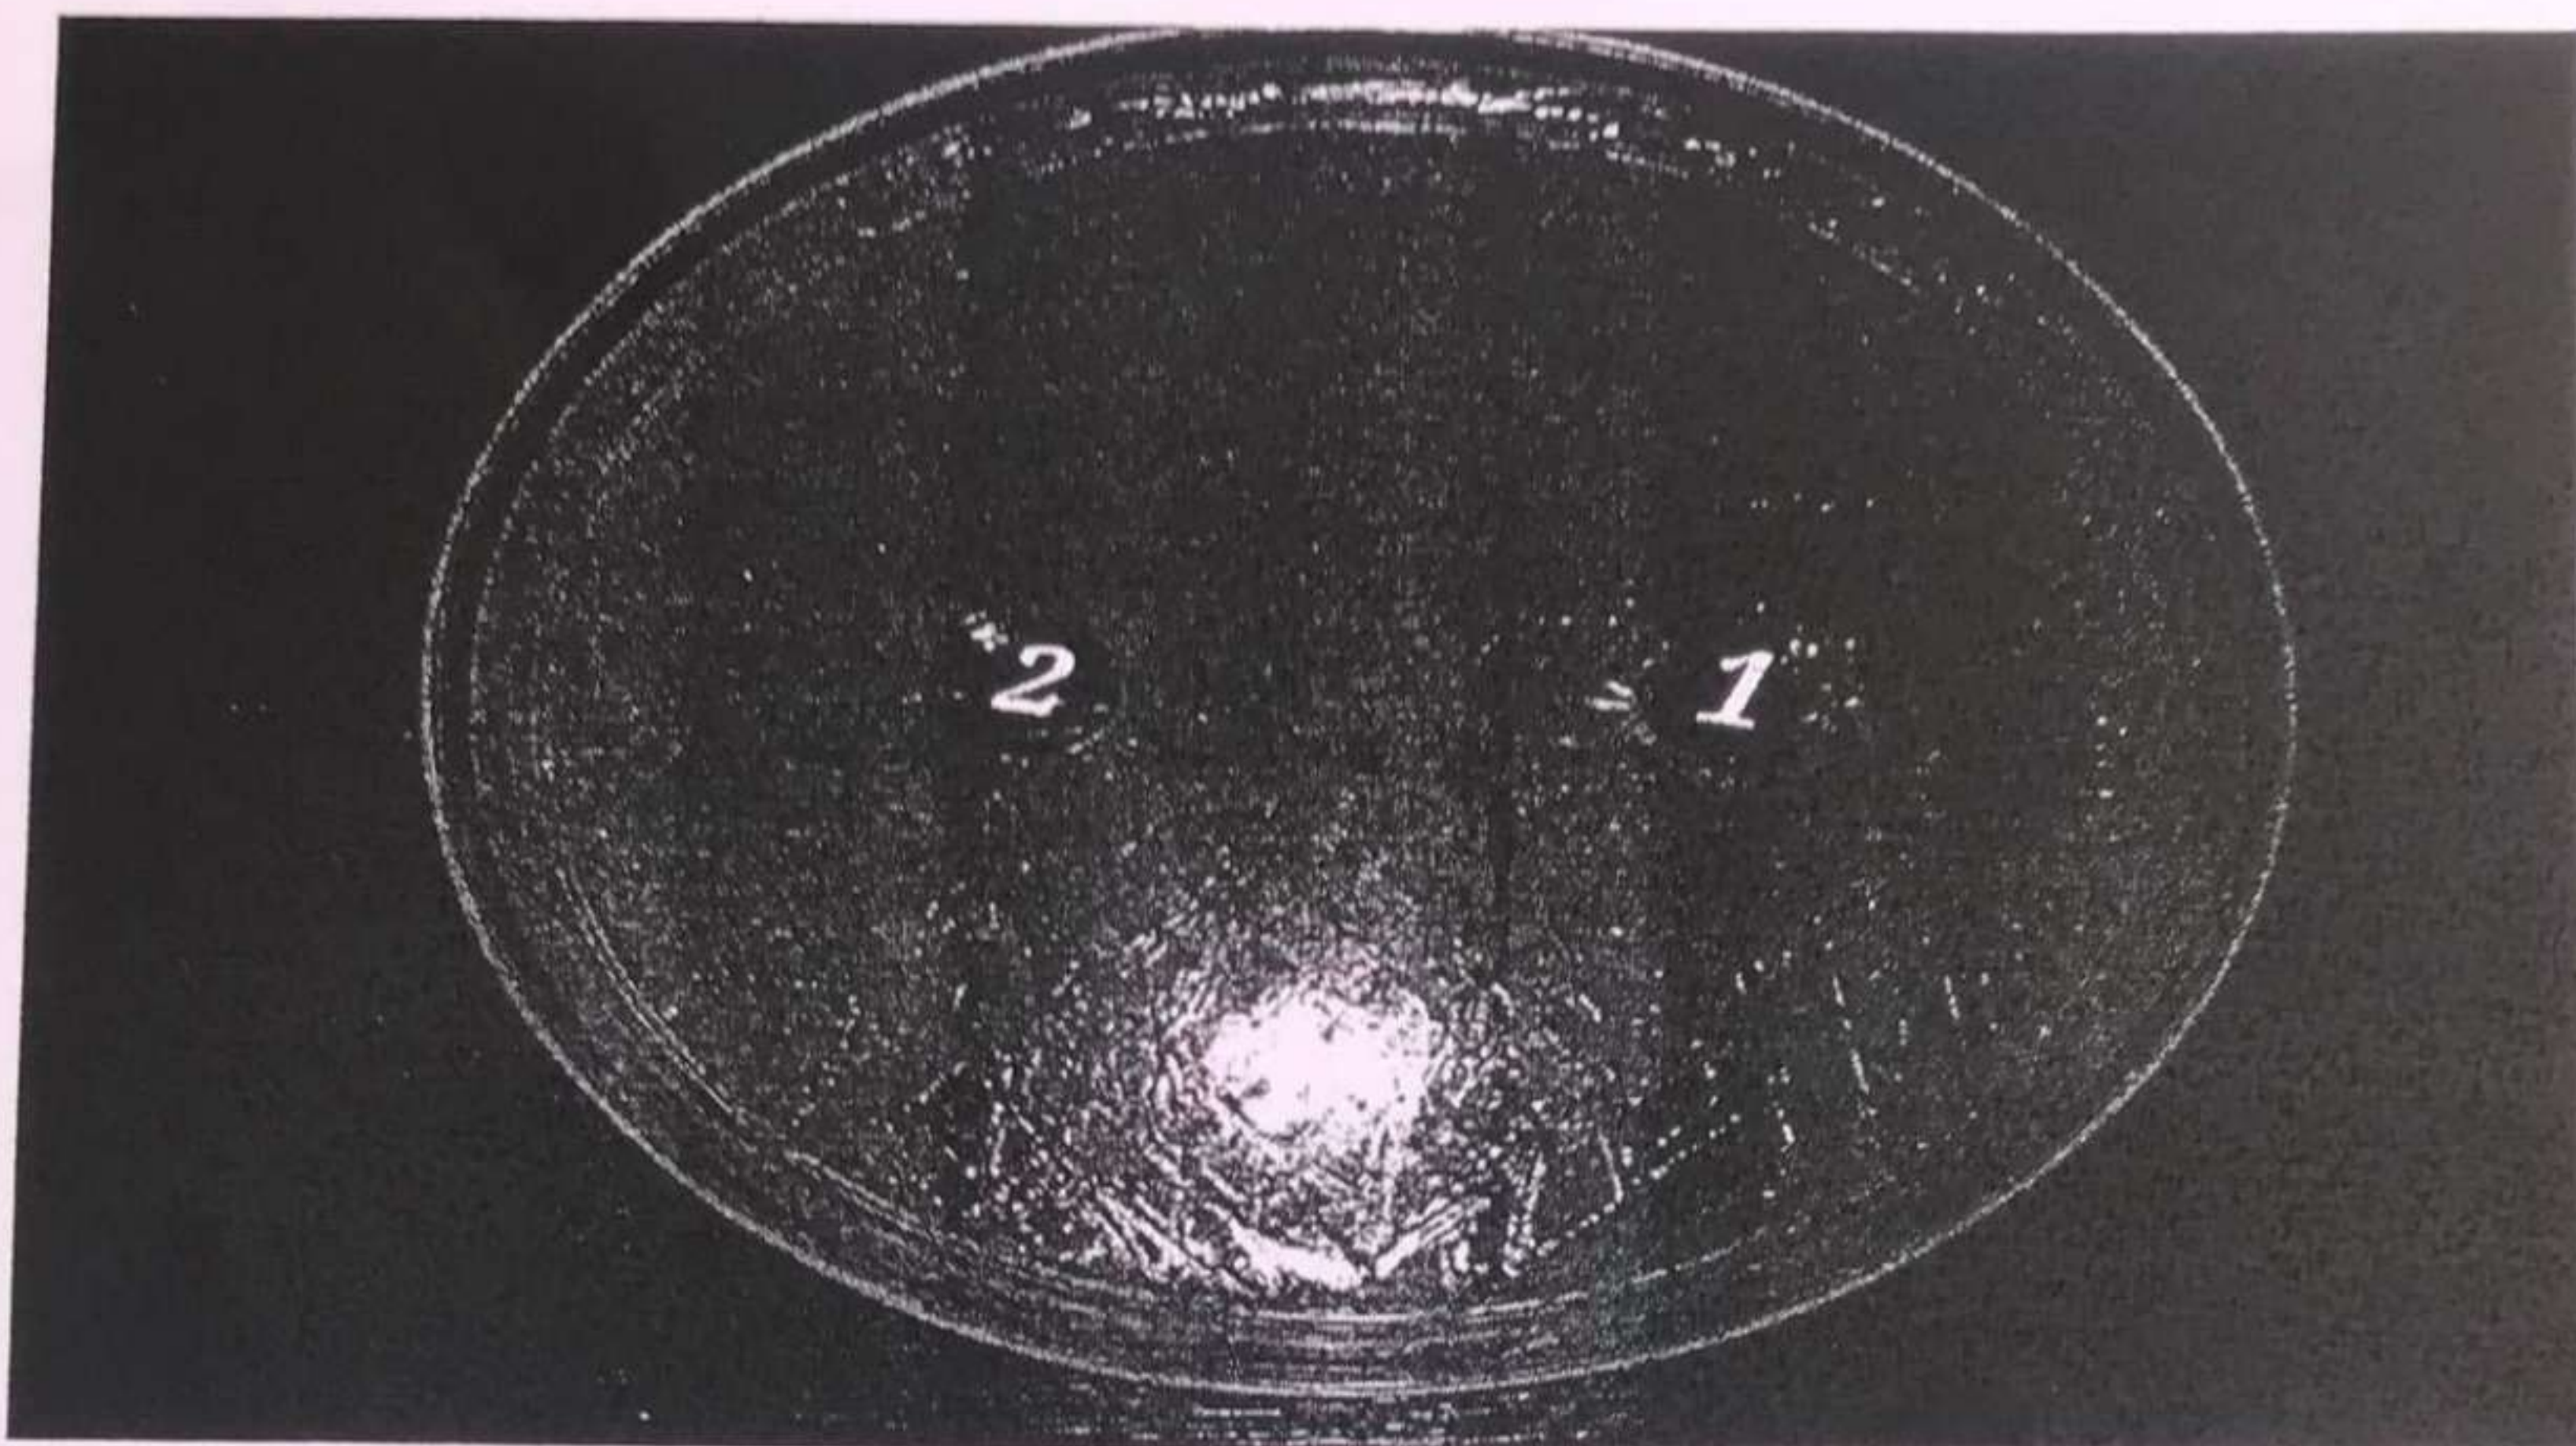


Figure (8). The antibacterial effect of Silver nanoparticles synthesis by Naringe leaf extract (1), Naringe leaf extract (2) using the test bacterium *Klebsiella pneumonia*.



Figure (9). The antibacterial effect of Silver nanoparticles synthesis by Naringe leaf extract (1), Naringe leaf extract (2) using the test bacterium *Staphylococcus aureus*.

explain the antimicrobial mechanism of positively charged Ag nanoparticles. Therefore, we expect that there is another possible mechanism. Amro *et al.* suggested that metal depletion may cause the formation of irregularly shaped pits in the outer membrane and change membrane permeability, which is caused by progressive release of lipopolysaccharide molecules and membrane proteins [27]. Also, Sondi and Salopek-Sondi speculate that a similar mechanism may cause the degradation of the membrane structure of *E. coli* during treatment with Ag nanoparticles [26]. Although their inference involved some sort of binding mechanism, still unclear is the mechanism of the interaction between Ag nanoparticles and component(s) of the outer membrane. Recently, Danilczuk and co-workers (2006) reported Ag-generated free radicals through the ESR study of Ag nanoparticles. We suspect that the antimicrobial mechanism of Ag nanoparticles is related to the formation of free radicals and subsequent free radical-induced membrane damage.

Our results support the hypothesis that Ag nanoparticles can be prepared in a simple and cost-effective manner and are suitable for formulation of new types of bactericidal materials.

Conclusions

This study describes a simple environmentally ecofriendly benign method of synthesis of silver nanoparticles from plants which is the best source. This method can be further used for industrial production of nanoparticles at room temperature and with a single step. This investigation provides evidence that plant extract stabilized nanoparticles may be ideal candidates for future studies exploring their use in biomedical and pharmacy applications. This synthesis procedure offers a less cost-effective and green alternative to traditional protocols that may be readily scaled up for industry as a result of the low synthesis temperatures and time required. Since Naringe (*Citrus aurantium*) leaf extract is easily available throughout the nation, the active nano compound from this can be prepared and used as effective antibacterial reagents even against multidrug resistant bacteria, and home-available, safe, cheap and with no side effect like the synthetic drugs.

References

- 1- Navaladian, S., B. Viswanathan, R.P. Viswanath, and T. K. Varadarajan, 2007. Thermal decomposition as route for silver nanoparticles. *Nanoscale. Res. Lett*; 2: 44-48.
- 2- Starowicz, M., B. Stypula, and J. Banas, 2006. Electrochemical synthesis of silver Nanoparticles. *Electrochem. Commun*; 8(2): 227-230.
- 3- Sreeram, K.S., M. Nidin, and B. U. Nair, (2008) .Microwave assisted template synthesis of silver nanoparticles. *Bull. Mater. Sci*; 31(7): 937-942.
- 4- Begum, N.A., S. Mondal, S. Basu, R.A. Laskar, and D. Mandal, 2009. Biogenic synthesis of Au and Ag nanoparticles using aqueous solutions of black tea leaf extracts. *Colloids Surf. B*; 71(1):113-118.
- 5- Huang, J., Q. Li, D. Sun, Y. Lu, Y. Su, X. Yang, H. Wang, Y. Wang, W. Shao, N. He, J. Hong, and C. Chen, 2007. Biosynthesis of silver and gold nanoparticles by novel sundried *Cinnamomum camphora* leaf. *Nanotech*; 18: 105104-105115.
- 6- Kasthuri, J., S. Veerapandian, and N. Rajendiran, 2009. Biological synthesis of silver and gold nanoparticles using apiin as reducing agent. *Colloids Surf. B*; 68: 55-60.

Silver nanoparticles are nanoparticles of silver which are in the range of 1 and 100 nm in size. Silver nanoparticles have unique properties which help in molecular diagnostics, in therapies, as well as in devices that are used in several medical procedures. The major methods used for silver nanoparticle synthesis are the physical and chemical methods. The problem with the chemical and physical methods is that the synthesis is expensive and can also have toxic substances absorbed onto them. To overcome this, the biological method provides a feasible alternative. The major biological systems involved in this are bacteria, fungi, and plant extracts. The major applications of silver nanoparticles in the medical field include diagnostic applications and therapeutic applications.

The synthesis of metal and semiconductor nanoparticles is an expanding research area due to the potential applications for the development of novel technologies. Generally, nanoparticles are prepared by a variety of chemical methods which are not environmentally friendly. We have reported a fast, convenient and extracellular method for the synthesis of silver nanoparticles by reducing silver nitrate with the help of Naringe (*Citrus aurantium*) leaf extract. The nanoparticles were characterized using UV-visible, FT-IR, XRD, AFM, and SEM methods. The surface plasmon resonance peaks in absorption spectra for silver colloidal solution showed that the absorption maximum range was at 380-440 nm. The functional biomolecules such as carboxyl groups present in the seaweed responsible for the silver nanoparticles formation were characterized by FT-IR. The XRD results suggested that the crystallization of the bio-organic phase occurs on the surface of the silver nanoparticles or vice versa. The broadening of peaks in the XRD patterns was attributed to particle size effects and the average particles size about 25.17 nm.

The results of the present study shows that silver nanoparticles synthesised by Naringe (*Citrus aurantium*) leaf extract has effective antibacterial activities on the test isolates as indicated by the diameter of their zone of inhibition. The inhibition zone was 14 mm for *Enterobacter cloacae*, 10 mm for *Escherichia coli*, 25 mm for *Klebsiella pneumonia*, 18mm for *Proteus mirabilis*, *Bacillus sp.*, *Staphylococcus aureus* and *Streptococcus spp.* 9 mm for *Pseudomonas aeruginosa*. Whereas the antimicrobial activity of Naringe (*Citrus aurantium*) leaf extract against test bacteria was negative Table (2) and Figure (8-11). Our interpretation of these results, the silver nanoparticles synthesised by Naringe (*Citrus aurantium*) leaf extract has another mechanism to kill bacteria not found in Naringe (*Citrus aurantium*) leaf extract. This finding agreement with the study conducted in the city of Hilla -Iraq, Hindi *et al.*, 2014 reached to the lowest antibacterial activity of Citrus leaves extract against most of the study bacterial isolates.

The mechanism of the inhibitory effects of Ag ions on microorganisms is partially known. Some studies have reported that the positive charge on the Ag ion is crucial for its antimicrobial activity through the electrostatic attraction between negative charged cell membrane of microorganism and positive charged nanoparticles [23, 24, 25]. In contrast, Sondi and Salopek-Sondi, (2004) reported that the antimicrobial activity of silver nanoparticles on Gram-negative bacteria was dependent on the concentration of Ag nanoparticle, and was closely associated with the formation of 'pits' in the cell wall of bacteria. Then, Ag nanoparticles accumulated in the bacterial membrane caused the permeability, resulting in cell death. However, because those studies included both positively charged Ag ions and negatively charged Ag nanoparticles, it is insufficient to

- 7- Nestor, A.R.V., V. S. Mendieta, M.A.C. Lopez, R. M. G. Espinosa, M.A.C. Lopez, and J.A. A. Alatorre, 2008. Solventless synthesis and optical properties of Au and Ag nanoparticles using *Camiellia sinensis* extract. *Mater. Lett*; 62: 3103-3105.
- 8- Shankar, S.S., A. Ahmad, and M. Sastry, 2003. Geranium leaf assisted biosynthesis of silver nanoparticles. *Biotechnol. Prog*; 19:1627-1631.
- 9- Chandran, S.P., M. Chaudhary, R. Pasricha, A. Ahmad, and M. Sastry, 2006. Synthesis of gold nanotriangles and silver nanoparticles using Aloe vera plant extract. *Biotechnol. Prog*; 22(2): 577-583.
- 10- Bar, H., D.K. Bhui, G.P. Sahoo, P. Sarkar, S. P. De, and A. Misra, 2009. Green synthesis of silver nanoparticles using latex of *Jatropha curcas*. *Colloids Surf. A*; 339: 134-139.
- 11- Jha, K.A. and K. Prasad, 2010. Green synthesis of silver nanoparticles using Cycas leaf. *Inter. J. Green. Nanotech*; 1(2): 110-117.
- 12- Pellati, F., S. Benvenuti, M. Melegari, and F. Firenzuoli, 2002. Determination of adrenergic agonists from extracts and herbal products of *Citrus aurantium* L. var. *J. Pharm. Biomed. Anal*; 29(6): 1113-1119.
- 13- Suryawanshi, J. A. S., 2011. An overview of *Citrus aurantium* used in treatment of various diseases. *African Journal of Plant Science*; 5(7): 390-395.
- 14- Jones, S.A., P. G. Bowler, M. Walker, and D. Parsons, 2004. Controlling wound bioburden with a novel silver-containing Hydrofiber dressing. *Wound Repair Regen*; 12(3):288- 94.
- 15- Silver, S. and L. T. Phung, 1996. Bacterial heavy metal resistance: new surprises. *Annu Rev Microbiol*; 50:753- 89.
- 16- Catauro, M., M. G. Raucci, F. D. De Gaetano, and A. Marotta, 2004. Antibacterial and bioactive silver-containing $\text{Na}_2\text{O} \times \text{CaO} \times 2\text{SiO}_2$ glass prepared by sol-gel method. *J Mater Sci Mater Med*; 15(7): 831-7.
- 17- Crabtree, J. H., R. J. Burchette, R. A. Siddiqi, I. T. Huen, L. L. Handott, and A. Fishman, (2003). The efficacy of silver-ion implanted catheters in reducing peritoneal dialysis-related infections. *Perit Dial Int*; 23(4): 368-74.
- 18- Padma S. V. and D. Shukla, 2012. Biosynthesis of silver nanoparticles using lemon leaves extract and its application for antimicrobial finish on fabric. *Appl Nanosci*; 2:163-168.
- 19- Srinivasan, D., S. Nathan, T. Suresh, and O. Perumalsamy, 2001. Antimicrobial activity of certain Indian medicinal plants used in folkloric medicine. *J. Ethnopharm*; 74:217- 220.
- 20- Barbara, M., R. Rothen, S. S. Church, B. Haenni, N. Kapp, and P. Gehr, 2006. Interaction of fine particles and nanoparticles visualized with microscopy techniques. *Environ Health Perspect*; 114: 1818-1825.
- 21- Langford, J. I. and A. J. C. Wilson, 1978. Scherrer after sixty years: A survey and some new results in the determination of crystallite size, *J. Appl. Cryst*; 11: 102-113.
- 22- Hindi, N. K. K., Z. A.G. Chabuck, and S. K.K. Hindi, 2014. Antibacterial Evaluation of Aqueous Extracts of Four Citrus Species in HILLA, IRAQ. *Intern. J. of Pharmacological Screening Methods*; 14(1): 43-48.

- 23- Hamouda, T., A. Myc, B. Donovan, A. Shih, J.D. Reuter, and Jr. J.R. Baker, 2000. A novel surfactant nanoemulsion with a unique non-irritant topical antimicrobial activity against bacteria, enveloped viruses and fungi. *Microbiol Res*; 156: 1-7.
- 24- Dibrov, P., J. Dzioba, K. K. Gosink, and C. C. Häse, 2002. Chemiosmotic mechanism of antimicrobial activity of Ag (+) in *Vibrio cholerae*. *Antimicrob Agents Chemother*; 46: 2668-70.
- 25- Dragieva, I., S. Stoeva, P. Stoimenov, E. Pavlikianov, and K. Klabunde, 1999. Complex formation in solutions for chemical synthesis of nanoscaled particles prepared by borohydride reduction process. *Nanostruct Mater*; 12: 267-70.
- 26- Sondi, I., and B. Salopek-Sondi, 2004. Silver nanoparticles as antimicrobial agent: a case study on *E. coli* as a model for Gram-negative bacteria. *J Colloid Interface Sci*; 275: 177-82.
- 27- Amro, N.A., L.P. Kotra, K. Wadu-Mesthrige, A. Bulychev, S. Mobashery, and G. Liu, 2000. High-resolution atomic force microscopy studies of the *Escherichia coli* outer membrane: structural basis for permeability. *Langmuir*; 16: 2789-96.
- 28- Danilczuk, M., A. Lund, J. Saldo, H. Yamada, and J. Michalik, 2006. Conduction electron spin resonance of small silver particles. *Spectrochimica Acta Part a*; 63: 189-91.